

Review

# IRON OXIDE NANOPARTICLES FOR DIAGNOSING AND TREATING DEGENERATIVE ORTHOPAEDIC DISEASES: A REVIEW

X.L. Zhu<sup>1</sup>, Q.C. Fu<sup>2,3,4,5</sup>, L.F. Jiang<sup>2,3,4,5,\*</sup> and L.M. Zheng<sup>2,3,4,5,\*</sup><sup>1</sup>Department of Radiology, The Second Affiliated Hospital, Zhejiang University School of Medicine, 310000 Hangzhou, Zhejiang, China<sup>2</sup>Department of Orthopedic Surgery, The Second Affiliated Hospital, Zhejiang University School of Medicine, 310000 Hangzhou, Zhejiang, China<sup>3</sup>Orthopedics Research Institute of Zhejiang University, 310000 Hangzhou, Zhejiang, China<sup>4</sup>Key Laboratory of Motor System Disease Research and Precision Therapy of Zhejiang Province, 310000 Hangzhou, Zhejiang, China<sup>5</sup>Clinical Research Center of Motor System Disease of Zhejiang Province, 310000 Hangzhou, Zhejiang, China

## Abstract

The prevalence of degenerative orthopaedic diseases, such as osteoarthritis, osteoporosis, and intervertebral disc disease, has increased due to the increasing prevalence and unsatisfactory therapeutic methods. Recently, different types of bioactive nanomaterials, such as iron oxide nanoparticles (IONPs), have raised much concern due to their ability to positively regulate the bone remodelling balance. Due to their magnetic characteristics, IONPs have been applied in magnetic resonance imaging in the clinic, but their ability to treat degenerative orthopaedic diseases has recently been shown both *in vitro* and *in vivo*. However, a comprehensive review of the potential utilization of IONPs in the orthopaedic field is lacking. Here, we summarize previous works in this review and discuss future research directions in this field.

**Keywords:** Iron oxide nanoparticles, magnetism, molecular diagnosis, orthopaedic diseases.

**\*Address for correspondence:** Lifeng Jiang, Orthopedic Department, The Second Affiliated Hospital, Zhejiang University School of Medicine, 310000 Hangzhou, Zhejiang, China; E-mail: jianglifeng@zju.edu.cn; Liming Zheng, Orthopedic Department, The Second Affiliated Hospital, Zhejiang University School of Medicine, 310000 Hangzhou, Zhejiang, China; E-mail: limzheng@zju.edu.cn.

**Copyright policy:** © 2024 The Author(s). Published by Forum Multimedia Publishing, LLC. This article is distributed in accordance with Creative Commons Attribution Licence (<http://creativecommons.org/licenses/by/4.0/>).

## Introduction

With the acceleration of ageing, the prevalence of degenerative orthopaedic diseases has increased rapidly, which has raised much concern. Degenerative orthopaedic diseases, which include many highly prevalent diseases, such as bone-featured osteoporosis (OP) and cartilage-featured osteoarthritis (OA)/intervertebral disc disease (IDD), are characterized by senescence of bone and cartilage tissues. These diseases cause many elderly people to suffer, which is also the main cause of disability and death.

OP is a common degenerative orthopaedic disease seriously threaten the survival quality of elderly (Agrawal and Garg, 2023; Ensrud and Crandall, 2024). Researchers have reported that fragility fractures occur more often in OP patients, especially in the hip and centrum, which can cause long-term bedrest and eventually death. Although many drugs, such as bisphosphonates, denosumab and teriparatide, are available, their side effects and limited therapeutic effects are still unsatisfactory (Pant *et al.*, 2023; Wei *et al.*, 2022; Zheng *et al.*, 2022). For example, in

the treatment of OP, the patients with long-termed application of bisphosphonates might suffer from atypical fracture in the shaft of femur (Aouad *et al.*, 2023; Black *et al.*, 2020). The fracture is always defined as low energy damage due to the patients' own gravity, which might owing to the over-inhibition of bone resorption, which affects the bone remodeling for the trabeculae bone with appropriate micro-architectural structure for load-bearing (Kordoni *et al.*, 2018; Lisnyansky *et al.*, 2018; Saleh *et al.*, 2013; Schilcher *et al.*, 2011).

OA is also a common degenerative disease of the whole joint characterized by pathological cartilage damage, which is the most common cause of joint disability and pain in elderly individuals and affects more than 250 million people worldwide (Allen *et al.*, 2022; Prieto-Alhambra *et al.*, 2014). In the clinic, stepped therapeutic methods highlight the importance of pharmacotherapy. However, the drugs such as nonsteroidal anti-inflammatory drugs (NSAIDs), glucosamine sulfate and sodium hyaluronate are always "safe but ineffective", which cannot intervene the

process of diseases, which makes it difficult to achieve a satisfactory therapeutic effect (Eckstein *et al.*, 2006; Ibrahiem *et al.*, 2023; Liu *et al.*, 2021; Moseng *et al.*, 2024; Pei *et al.*, 2023; Shavlovskaya *et al.*, 2023; Wu *et al.*, 2023). Those patients can barely avoid receiving the surgical treatment due to the progression of diseases and the disease-modifying drugs is still in development (Li *et al.*, 2023; Makarczyk *et al.*, 2021; Shavlovskaya *et al.*, 2023). The situation of IDD is similar to that of OA. Hence, the novel pharmacological therapeutic method is in urgent need for those degenerative orthopedic diseases.

Recently, with the development of nanotechnology, the treatment of degenerative orthopaedic diseases has become possible. These nanomaterials easily pass through physiological barriers due to their unique physicochemical properties, such as a high surface-to-volume ratio, which allows them to be applied in drug delivery and enhances their therapeutic effect (Bartkowski *et al.*, 2024; Liang *et al.*, 2023b). As a typical nanomaterial, iron oxide nanoparticles (IONPs), including  $\text{Fe}_3\text{O}_4$ ,  $\gamma\text{-Fe}_2\text{O}_3$ , and hybrid ferrites, have garnered much attention. These nanoparticles can carry iron, which can be detected by existed medical device such as magnetic resonance imaging (MRI). Also, it can induce biological activities due to the release of iron ions and the properties of nanoparticles. In previous translational research, IONPs exhibited excellent biocompatibility and biodegradability *in vivo* (Paik *et al.*, 2015; Patil *et al.*, 2015). Additionally, they are sensitive to magnetic fields, enabling their use in both diagnostic and therapeutic approaches, especially for the cellular and subcellular diagnosis (Kim *et al.*, 2020; Shi *et al.*, 2020; Vallabani *et al.*, 2019; Wu *et al.*, 2015). Meanwhile, due to the modifiable property, the IONPs have been used to prepare a lot of multi-functional agents with the integration of diagnosis and treatment have been developed, especially in the oncological field.

Although the IONPs have been maturely applied in the biomedical field, the research is in its infancy in orthopedic field. According to previous reports, IONPs has been explored to be applied in the diagnosis and treatment of different orthopedic diseases, such as OA, OP, bone tumors, fractures, osteolysis, and bone defects (Fig. 1) (Guo *et al.*, 2020; Pang *et al.*, 2021; Sadeghzadeh *et al.*, 2023; Vergnaud *et al.*, 2022; Wang *et al.*, 2021a; Zhang *et al.*, 2024). The nanoparticles exhibited great bioactivity when locally administrated in bone tissues alone or combined with other motifs, such as the enhancement of osteogenic and chondrogenic differentiation. Also, the unique magnetic properties make the IONPs could be used for magnetic-respond drug/stem cell tracing and delivery in orthopedic diseases (Chang *et al.*, 2021; Xia *et al.*, 2019b). When combined with the intervention of external magnetic field, the IONPs might translate the magnetic into other stimulation via different electromagnetic effect, such as the magnetocaloric effect, magneto-force effect (Del Bianco *et*


*al.*, 2022; Hamad *et al.*, 2021; Ma *et al.*, 2022; Wang *et al.*, 2021b). The physical intervention is especially emphasized in the abundance of bone matrix, which finally act on the cells and induced the alteration in the cellular behaviors, such as the regulation of osteogenic and chondrogenic differentiation (Harris *et al.*, 2015).

Although the IONPs is a promising agent due to the magnetic properties and biological activity, the biosafety and efficiency in diagnosing and treating degenerative orthopedic diseases are still worrying. As is known, the iron ions are tightly related to the ferroptosis, which has been regarded as the key pathological process in the inflammation and senescence (Coradduzza *et al.*, 2023; Fan *et al.*, 2024; Sun *et al.*, 2024). In the oncological field, the ferroptosis is an effective weapon for killing the tumor cells. However, in the treatment of degenerative diseases, it might be regarded as a “double-edged sword”, which might contribute to the acceleration of pathological process. Also, too many kinds of IONPs have been developed for the biomedical application due to the excellent extensibility. However, how to use an appropriate IONPs agent to intervene the determined pathological process in the degenerative orthopedic disease is still unclear. Briefly, a retrospective review based on the translational application perspective in orthopaedic field is still in lack. Herein, we summarize the application of IONPs in diagnosing and treating degenerative orthopaedic diseases, which might provide new insights for future research in this field.

## The Preparation of IONPs

IONPs can be prepared by various methods, including physical, chemical and biological methods, which is tightly linked with the physicochemical properties (Laurent *et al.*, 2008; Wu *et al.*, 2015). Due to the lack of ability to precisely control the size of IONPs in the nanoscale, the physical approaches, such as the electron beam lithography, aerosol, gase phase deposition, and powder ball milling, are not widely applied (Ling *et al.*, 2015). The biological process relies on the redox reaction, which is more promising to be explored in the future. We considered that the *in-situ* synthesis of IONPs *in vivo* might be a ultimate aim of the biological method. However, the present application is still limited, and the application of physical and biological methods account for less than 10% in the preparation of IONPs (Ali *et al.*, 2016; Revathy *et al.*, 2023; Samrot *et al.*, 2021). Hence, we focus on introducing the chemical synthesis routes.

The co-precipitation method is among the most simple and efficient synthesis procedures, which involves the mixing of multiple metal salts and precipitants to trigger a reaction, ultimately leading to the formation of a mixture comprising iron oxide and metal ions in the reaction solution (Sharouf and Saffour, 2024; Wahfiudin *et al.*, 2024). The adjustment of factors such as pH value, reaction time, precipitant type, and solution concentration en-

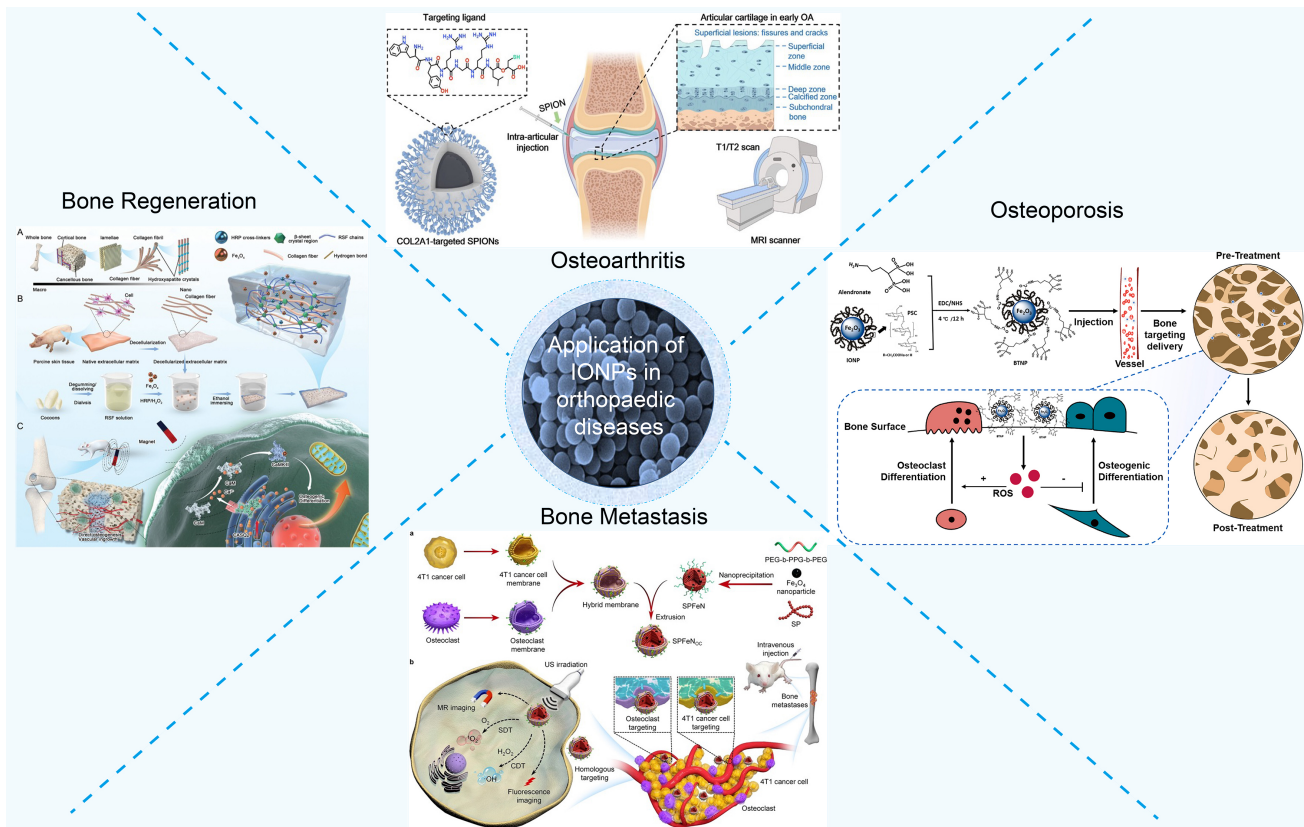

**Fig. 1.** Application of iron oxide nanoparticles (IONPs) for treating orthopaedic diseases.

ables the achievement of control over product particle size and composition (Wahfiudin *et al.*, 2024). Nevertheless, this method is associated with a broad particle size distribution and challenges in precisely controlling product composition. To overcome these challenges, the improved co-precipitation techniques with the assistance of magnetic field, ultrasound, or functionalized bases have been developed (Liu *et al.*, 2011; Pereira *et al.*, 2012; Petcharoen and Sirivat, 2012; Remya *et al.*, 2016; Roy *et al.*, 2016; Suh *et al.*, 2012; Wu *et al.*, 2011).

To precisely control the size and shape of IONPs, the solvothermal method, which is also named as thermal decomposition, was developed (Hufschmid *et al.*, 2015; Park *et al.*, 2004). The method entails the heating of a solution comprising a mixture of metal ions and surfactants to yield IONPs with tunable particle sizes. By manipulating parameters such as temperature, concentration, surfactant type, and heating duration, this method allows for the precise attainment of desired product particle sizes and shape (Sharifi *et al.*, 2012). However, this approach necessitates high temperatures and a complex preparation process, which make it not environmentally friendly. Also, the application of toxic chemicals in the synthesis processes make its own a risk in biocompatibility to be directly applied in the medical scene (Roy *et al.*, 2021).

The sol-gel method is also a common method for the preparation of IONPs, which involves the swelling of

metal ions in an organic solvent, followed by hydrolysis and repolymerization to form an iron oxide gel system (Darmawan *et al.*, 2010; Puscasu *et al.*, 2016). Subsequent heat treatment leads to the production of nanoparticles. This approach exhibits high precision and controllability, enabling the regulation of product morphology and crystal form through the manipulation of conditions such as hydrolyzing agent type and concentration (López-Sánchez *et al.*, 2022; Panda *et al.*, 2024; Waqas *et al.*, 2024). However, it necessitates a prolonged preparation time, a complex process, and may result in environmental pollution due to the use of organic solvents.

Besides, a lot of methods such as microemulsion, hydrothermal, sonochemical and electrochemical deposition methods were employed for the preparation of IONPs. The microemulsion method used two immiscible liquids to form a confined environment for the nucleation and controlled growth of nano- and micro-particles (Hwang, 2024; Morán *et al.*, 2023; Rahman *et al.*, 2024). Although the size of the IONPs could be easily controlled by regulating the micelles, the limited crystallinity and yield make it hard to be translated in clinic use (Chaudhari and Panda, 2023). The hydrothermal method is relatively low-cost and easy to be performed. However, the final size of particles is not easy to be controlled (Hang *et al.*, 2024; Ta *et al.*, 2024). We have listed the advantages and disadvantages of different methods in the Table 1 for the future reference. The more

**Table 1. The comparison of different synthesis method of iron oxide nanoparticles (IONPs).**

Method	Complexity	Energy intensity	Homogeneity	Shape control	Crystallinity	Yield
Co-precipitation	Very simple	Low	Bad	Bad	Low	High
Solvothermal	Very complicated	High	Excellent	Excellent	High	High
Sol-gel	Relatively simple	Low	Good	Good	Low	Low
Microemulsion	Complicated	Low	Good	Good	Low	Low
Hydrothermal	Relatively simple	High	Good	Bad	High	High

preparation methods with ability to balance the yield and the ability to control the size and shape of IONPs is still in need to be developed.

### The Biocompatibility of IONPs

When IONPs are applied in biomedical applications, biosecurity, which includes adverse effects when animals are exposed to nanoparticles, is highly important. Thus, we used a single section to exhibit the biocompatibility of IONPs before the application in orthopedic field. A previous review reported the therapeutic efficacy, migration and metabolism of IONPs *in vivo* (Malhotra *et al.*, 2020). Although IONPs have been used in different ways in the biomedical field, toxicity is still a challenge that hinders their clinical translation. Although many types of IONPs exist, they have similar structures, including iron oxide cores, polymer coatings, and external layers. Previous work has shown that the toxicity of IONPs is mostly dependent on the shape and size of the nanoparticles and the presence of coating materials (Hussain *et al.*, 2005; Jeng and Swanson, 2006; Karlsson *et al.*, 2008; Karlsson *et al.*, 2009; Malehmir *et al.*, 2023). Herein, we separately introduce the aspects for the reference to prepare more bio-friendly IONPs for treating degenerative orthopaedic diseases.

The size of IONPs is an important factor affecting the cellular toxicity, which is mainly related to metabolism *in vivo*. In general, smaller IONPs (<10 nm) are metabolized by renal extravasation, while larger IONPs (>200 nm) are captured by the spleen, which indicates that IONPs with a size of 10-100 nm are more suitable for application *in vivo* (Choi *et al.*, 2007; Gupta and Gupta, 2005). Additionally, many studies have shown that different shapes of IONPs are linked to toxicity. For example, spherical IONPs have been observed to have lower toxicity than other shapes, while rod-shaped IONPs have been reported to have greater toxicity (Ran *et al.*, 2015).

Previously, it was reported that a polymer coating is the most important structure for relieving the toxicity of iron oxide and could also prevent the aggregation of nanoparticles (Gupta and Gupta, 2005). The possible potential mechanisms include enhancing the stability of IONPs and reducing the speed of iron ion release from the iron oxide core. Previous results have shown that the albumin nanoparticle coating provides a stable biocompatible shell and prevents the cytotoxicity of magnetite nuclei. After prolonged exposure (48 hours), IONPs become cytotoxic due to the produc-

tion of free radicals, but this toxic effect can be neutralized by the use of polyethylene glycol (Abakumov *et al.*, 2018). Previously, we found that polymer coatings could relieve iron overload-induced OP by scavenging reactive oxygen species (ROS) (Yu *et al.*, 2020). As is widely known, the ferroptosis is a kind of cellular death based on the lipid peroxidation and the generation of ROS, which means that the ROS-scavenging polymers are also promising in reducing the toxicity by intervene the cellular behavior (Cao *et al.*, 2024; Endale *et al.*, 2023; Teschke, 2024). So, a lot of polymer materials with excellent antioxidant properties is also promising to be used for the synthesis of novel IONPs with more excellent biocompatibility and diversified bioactivity, and the area is worth to be explored in the future. Each coating material has its own advantages and disadvantages, and we should pay attention to the selection (Abakumov *et al.*, 2018). However, studies on the relationship between coating materials and toxicity in different microenvironments are still limited, and more studies need to be conducted.

The biosafety of IONPs is a crucial aspect that should be thoroughly examined and addressed for their successful clinical translation (Wang *et al.*, 2024a; Yang *et al.*, 2023). While IONPs offer immense potential in various biomedical applications, such as drug delivery, magnetic resonance imaging, and hyperthermia treatment, their long-term safety profile remains a significant concern (Marycz *et al.*, 2020; Moacă *et al.*, 2023). IONPs are typically designed to degrade over time, releasing iron ions that are subsequently metabolized by the body. However, uncontrolled degradation can lead to excessive accumulation of iron, potentially causing oxidative stress and cellular damage. Therefore, strategies to precisely regulate the degradation rate of IONPs are crucial. As is shown in Fig. 2, a work used a continuous flow system to unveil the biologically degradation behavior *in vivo* and characterize the degraded products, which is important in promoting the clinical application of IONPs (Yang *et al.*, 2024). The improvement of biosafety can be realized by the application of novel coatings or modifications that stabilize the nanoparticles for a desired duration, ensuring that they degrade only when needed (Gu *et al.*, 2024; Natarajan and Tomich, 2020; Zhong *et al.*, 2019). Moreover, the use of targeting ligands that specifically deliver IONPs to target cells while minimizing accumulation in healthy tissues could also be explored (Israel *et al.*, 2020; Liao *et al.*, 2015; Park *et al.*, 2008; Riegler *et al.*, 2013; Zhi *et al.*, 2020; Zhou *et al.*,

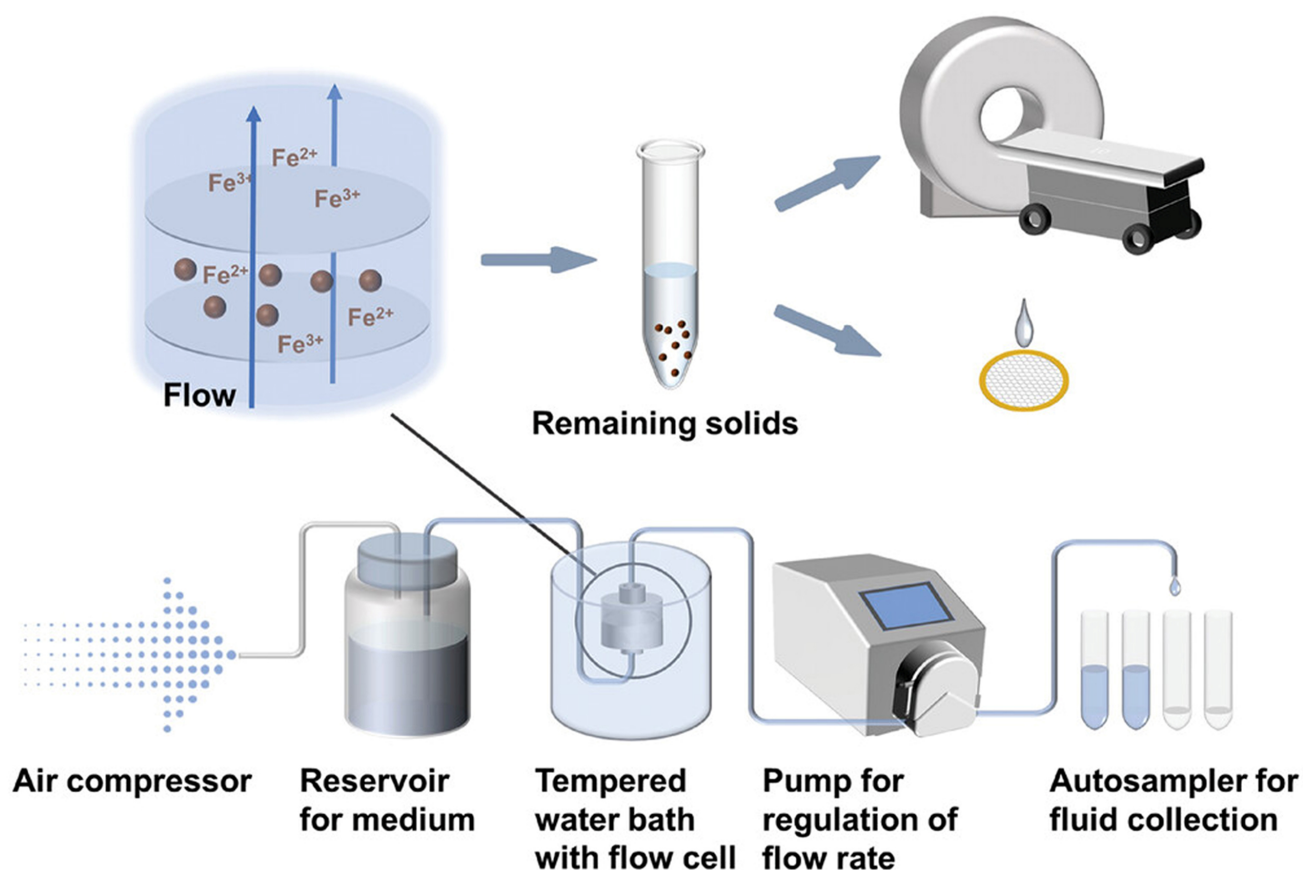


Fig. 2. A flow system which can dynamically monitor the degradation behavior of IONPs *in vivo*. Image cited from Yang *et al.* (2024).

2022). The biosafety of IONPs is a multifaceted issue that requires a comprehensive approach to address. By controlling the degradation rate, avoiding long-term accumulation, and mitigating potential toxic side effects, researchers can enhance the safety profile of IONPs and pave the way for their successful clinical translation.

### Magnetic Nanoparticles for Imaging Innovations

In enhanced Magnetic Resonance (MR) detection, the most widely applied contrast agent is gadolinium (III). However, its high toxicity, especially in patients with liver and kidney failure, has raised significant concerns and limited its clinical application (Chen *et al.*, 2011; Di Marco *et al.*, 2017). In previous work, ultra-superparamagnetic iron oxide nanoparticles (SPIONs) were shown to significantly reduce the transverse relaxation time (T2) during MRI (Ajayi *et al.*, 2023), and these materials have the potential to be applied as novel contrast agents. Recently, the imaging properties of newly prepared IONPs have been shown to be similar to those of gadolinium-based contrast agents, which are in the process of clinical translation (Liu *et al.*, 2013)

IONPs can be used for MRI of different tissues. Usually, nanoparticles less than 10 nm in size are excreted in

the urine, while a large number of nanoparticles larger than 200 nm are engulfed by the digestive system. This phenomenon indicated that the IONPs used for imaging different organs need to be of different sizes and shapes. Larger IONPs accumulate in the reticuloendothelial system (RES), which enables the imaging of the liver and spleen (Dadfar *et al.*, 2019). Moreover, particles with sizes between 20 and 150 nm tend to deposit in connective tissues (bone, tendons, and muscles), stomach, and kidneys, as reported previously (Wang *et al.*, 2022a). As mentioned above, the size of IONPs could be easily controlled by adjusting the preparation process. Determining the relationship between the size of IONPs and their enrichment in organs is important for future research and is highly valuable for preparing individual products for organ imaging.

In bone tissue imaging, imaging depth is still a challenge that limits imaging technology, but IONPs might provide a possible solution. Recently, magnetic particle imaging (MPI) technology, which aims to evaluate the electromagnetic properties of IONPs according to the gradient relationship between the magnetic field and concentration of IONPs, has been developed. IONPs saturate according to the direction of the magnetic gradient, except in a field without a magnetic field (Graeser *et al.*, 2019; Panagiotopoulos *et al.*, 2015; Saritas *et al.*, 2013). The oscillating be-

haviours of IONPs make it possible to visualize and quantify the imaging results, which eliminates common issues in optical imaging, such as the disturbance of autofluorescence and signal attenuation in tissues (Bulte *et al.*, 2015; Saritas *et al.*, 2013). Moreover, MPI technology is not dependent on negative contrast for screening IONPs, which could avoid confusion in visualization at the air medium and tissue interfaces (Talebloo *et al.*, 2020). Moreover, MPI enables continuous longitudinal screening of signals in samples, which is vital for cell tracing *in vivo* (Kang *et al.*, 2014; Rana *et al.*, 2010). Previously, the IONPs conjugated with collagen-binding peptides and IONPs can be detected via MRI methods for the diagnosis and treatment of osteoarthritic joints (Guan *et al.*, 2023). We hope similar studies will contribute to the diagnosis of the pathological process of orthopedic diseases.


### Application of IONPs in the Treatment of OA

OA is a representative degenerative orthopaedic disease characterized by the deterioration of cartilage and subchondral bone (Abdelbari *et al.*, 2023). Cartilage tissues are regarded as avascular connective tissue without a self-renewal ability, but cartilage regeneration has become a challenge (Bullock *et al.*, 2018). Herein, we investigated the application of IONPs in the treatment of OA and in the treatment of cartilage-derived degenerative orthopaedic diseases, including as nanocarriers and diagnostic/therapeutic agents.

Due to the absence of the vasculature, the entry of agents into the joint carve has been regarded as a complex problem. Methods to deliver drugs into the joint carve have raised much concern. The systemic administration of drugs is limited by systemic side effects and low bioavailability (Abbas *et al.*, 2022b; Mosallam *et al.*, 2022; Yang *et al.*, 2011). Local intra-articular injection is a promising method for directly delivering bioactive agents to cartilage lesions. However, repeated punctures increase the risk of iatrogenic infection. Nanocarriers have been developed for efficient drug delivery via the joint route to address these challenges, and they improve drug delivery efficiency while minimizing adverse effects on other organs and tissues (Abbas *et al.*, 2022a; Mohamed *et al.*, 2020). Magnetic targeting combined with IONPs has been shown to be efficient for drug delivery (Ong *et al.*, 2020; Suryadevara *et al.*, 2023). IONPs, which are easy to fabricate, play a vital role in the controlled delivery of bioactive agents to the determined area and have shown advantages in terms of biocompatibility and surface functionalization (Abbas *et al.*, 2022a, Das *et al.*, 2019, Son *et al.*, 2015). Molecular drugs can easily bind directly to the iron oxide surface for local delivery (Ibrahiem *et al.*, 2023; Partain *et al.*, 2020). In addition, Mei *et al.* (2016) prepared IONPs with superparamagnetic properties using a high-temperature thermal decomposition method and subsequently coated them with PEG. The modified IONPs had a particle size of  $5.9 \pm 1.1$

nm and could easily penetrate into cartilage for drug delivery. Additionally, other works have used WYRGRL, which is a short peptide that combines with COL2A1 in the extracellular matrix of cartilage (Papadimitriou *et al.*, 2014; Yarmola *et al.*, 2016). Also, the IONPs conjugated with C5-24 peptides increased the retention of hyaline cartilage when administrated in OA knees in a previous study (Guan *et al.*, 2023). Additionally, IONPs contribute to cartilage repair and regeneration by recruiting bone mesenchymal stem cells (BMSCs) to specific locations and promoting their expression while causing fewer inflammatory responses (Yang *et al.*, 2019a and Yang *et al.*, 2019b). These innovative approaches present promising avenues for advancing OA treatment.

In addition to drug delivery, IONPs have also been widely used directly for diagnosing and treating OA (Fig. 3). The use of COL2A1-targeting IONPs can aid in the use of MRI to distinguish cartilage with early degenerative characteristics from healthy cartilage to achieve molecular-level diagnosis (Wu *et al.*, 2023). Additionally, chitosan-modified IONPs have been shown to be efficient at labelling cells without altering their differentiation ability, which can be useful for intra-articular imaging. Interestingly, a team used IONPs to collect CTX-II, an important biomarker in osteoarthritic joint carves, which is called “magnetic capture” and is helpful for the early-stage diagnosis of OA (Garraud *et al.*, 2016; Yarmola *et al.*, 2016). As metal oxide nanoparticles, IONPs were proven to significantly improve histopathological damage to rat knee joints by regulating OPG, RANKL, ERK1, and MAPK levels (Ibrahiem *et al.*, 2023). In addition, IONP-containing biomaterials, such as diphasic magnetic nanocomposite scaffolds, nanovehicles, and PLGA microspheres, have been developed for the treatment of OA (Butoescu *et al.*, 2009; Huang *et al.*, 2018; Zhang *et al.*, 2020; Wang *et al.*, 2024b). *In vitro* experiments have shown that IONPs can promote the differentiation of BMSCs into chondrocytes and upregulate the Ihh/PTHrP signaling pathway, providing a potential therapeutic approach for treating cartilage degeneration-related diseases (Jiang *et al.*, 2017). Additionally, studies have explored the effects of IONPs on the chondrogenic differentiation of human bone marrow stromal cells (HBMSCs), neonatal, and adult chondrocytes. It was found that the viability of all cell types was unaffected; however, the cell morphology shifted to a “stretched” phenotype after SPIO uptake, and the proliferation of neonatal chondrocytes decreased after SPIO uptake (Saha *et al.*, 2013). *In vivo* studies have found that 12.75  $\mu\text{g/mL}$  M-SPIO can successfully label human articular cartilage-derived chondroprogenitor cells with minimal impact on cell viability, MSC marker expression, and differentiation potential (Vinod *et al.*, 2019). It also does not affect the production of major cartilage matrix components (Ramaswamy *et al.*, 2009). However, the potential regulatory mechanism has not been elucidated well, and whether the therapeutic effects are due to nanopar-

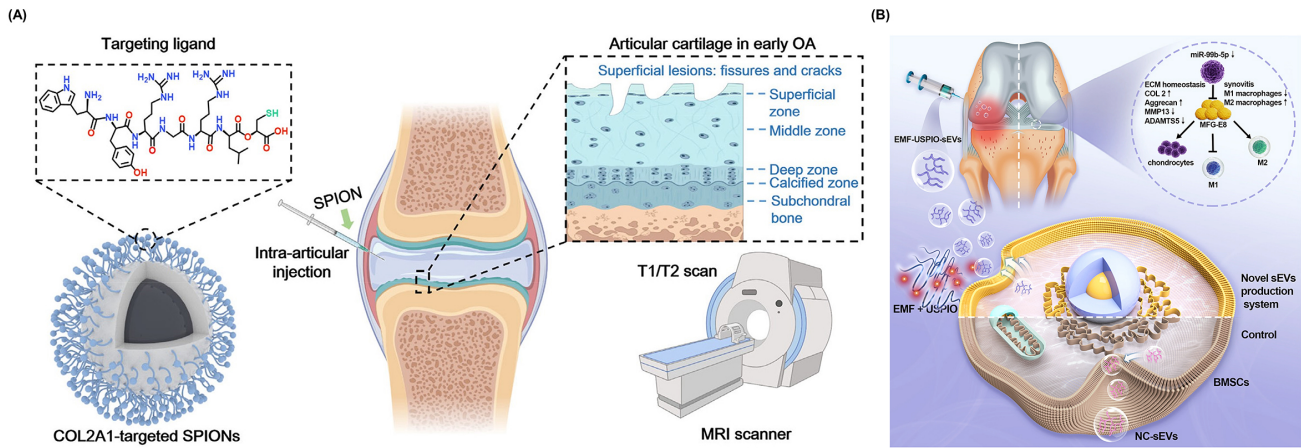

**Fig. 3.** IONPs have been proven effective in treating osteoarthritis (OA). (A) COL2A1 targeted IONPs for treating OA. Image cited from Wu *et al.*, (2023). (B) IONPs based hybrid system for treating OA. Image cited from Wang *et al.* (2024b).

ticle properties or degradation products remains unclear and is worth exploring (Table 2).

In addition to the application of IONPs as drugs to treat OA, IONPs are more likely to be applied in combination with stem cells or chondrocytes in the cell tracing field and can exhibit therapeutic effects. IONPs combined with MRI T2 imaging can maintain the stemness of adipose-derived stem cells (ADSCs), which is promising for application in MRI-assisted cartilage tissue engineering (Xie *et al.*, 2019). Naosuke Kamei *et al.* prepared a cell delivery system to deliver mesenchymal stem cells (MSCs) to the cartilage defect area for cartilage repair (Kobayashi *et al.*, 2008). They subsequently conducted clinical work and reported that IONP-labelled autologous MSCs were safe for repairing cartilage defects in the knee, while newly formed cartilage was observed 48 weeks after surgery (Kamei *et al.*, 2018). Additionally, IONP-labelled chondrocytes can also be guided by a magnetic field to the cartilage defect area for cartilage repair (Gong *et al.*, 2018). As the autologous chondrocyte implantation (ACI) technique has been regarded as effective for treating cartilage defects, the use of IONP-labelled chondrocytes is similar to that of chondrocyte transplantation, which seems to have the advantage of minimal invasion. Briefly, IONPs combined with stem cells or chondrocytes are easy to translate in the clinic. However, long-term studies on the safety and effectiveness of these treatments are still needed.

### Application of IONPs in the Treatment of OP

OP is a common bone degenerative disease with an extremely high prevalence in elderly individuals. OP can be divided into two subtypes: decreased bone formation activity and increased bone resorption activity (Compston *et al.*, 2019; Ensrud and Crandall, 2024). Previously, IONPs were shown to be effective in regulating the behaviour of osteoblasts and osteoclasts. Chitosan-coated IONPs modified with chitosan and hydroxyapatite were reported to

be effective at enhancing the proliferation of osteoblasts while protecting the cells from exogenous stimuli and promoting osteogenic differentiation (Shi *et al.*, 2012; Tran *et al.*, 2012; Tran and Webster, 2011). Similar osteogenic-enhanced effects of IONPs were found in osteoporotic fracture models, while implant osseointegration was significantly enhanced (Anjum *et al.*, 2023; Fouad-Elhady *et al.*, 2020; Hedvičáková *et al.*, 2023, Paun *et al.*, 2018). Moreover, with the assistance of a magnetic field, IONPs can be guided to any bone area needed to enhance the formation of bone tissue, which could reverse the process of OP (Tran and Webster, 2013). In the same period from approximately 2012-2015, bone-targeting IONPs were developed for the radiological evaluation of bone metabolic activity (Panahifar *et al.*, 2013). Additionally, the inhibitory effect of IONPs on osteoclasts was reported to be dependent on the TRAF6-p62-CYLD pathway (Li *et al.*, 2021; Liu *et al.*, 2019). However, with the increased awareness of iron overload-induced OP, the application of IONPs in treating this disease is controversial. In 2020, we reported that IONPs coated with antioxidative polysaccharides can release iron ions in bone mass without causing iron accumulation-related OP, which might be explained by the ROS scavenging effect of polysaccharides (Yu *et al.*, 2020). Subsequently, IONPs combined with typical anti-OP drugs, such as bisphosphonates, were prepared for the treatment of OP in our and other works (Lee *et al.*, 2016; Zheng *et al.*, 2022, Panseri *et al.*, 2012). Furthermore, Guan H *et al.* (2023) combined IONPs, Piezo1 activators and zoledronic acid in a hybrid system for the treatment of OP, which was shown to have an excellent therapeutic effect. Also, Yuanyuan Guo *et al.* (2021) used the IONPs to remote-controllable deliver estradiol to treat OP in rats models and achieved a success. However, the potential mechanism by which IONPs regulate OP is still unclear. In our previous work, we found that IONPs could regulate the inflammatory microenvironment in bone tissues,

**Table 2. The researches of the effect of IONPs on chondrogenic differentiation.**

IONPs	Magnetic field intensity	Cell type	The effect of IONPs on the chondrogenic differentiation	Reference	
Magnetospirillum IONPs	sp-isolated	0.25 mT	BMSCs	Enhanced	(Son <i>et al.</i> , 2015)
Carbon quantum dots-doped IONPs		0.05 T	WJ-MSCs	Enhanced	(Das <i>et al.</i> , 2019)
Ferumoxytol		None	MSCs	Enhanced	(Suryadevara <i>et al.</i> , 2023)
Superparamagnetic iron oxide		None	BMSCs	Transient inhibition	(Saha <i>et al.</i> , 2013)
Superparamagnetic iron oxide		1 T	ADSCs	Inhibited	(Kolecka <i>et al.</i> , 2017)
Kartogenin-loaded super-paramagnetic iron-oxide	ultra-small	None	BMSCs	Enhanced	(Suryadevara <i>et al.</i> , 2023)

BMSCs, bone mesenchymal stem cells; MSCs, mesenchymal stem cells; ADSCs, adipose-derived stem cells; WJ-MSCs, Wharton's jelly mesenchymal stem cells.

which is beneficial for bone renewal and the function of bisphosphonates (Fig. 4). IONPs can be combined with different materials, such as calcium phosphate cement (CPC) (Xia *et al.*, 2019a), or synthesized into mesoporous silica-coated magnetic ( $\text{Fe}_3\text{O}_4$ ) nanoparticles (M-MSNs) (Jia *et al.*, 2019), both of which enhance the osteogenic activity of stem cells through the WNT/ $\beta$ -catenin signaling pathway. Marycz K *et al.* (2020) synthesized the  $\alpha\text{-Fe}_2\text{O}_3/\gamma\text{-Fe}_2\text{O}_3$  nanocomposite does not induce an immune response and regulates integrin expression; it also enhances the osteogenic differentiation of osteoblasts and triggers apoptosis of osteoclasts. The combined use of a 1-2 T static magnetic field (SMF) and IONPs reduces iron uptake by osteoclasts and decreases oxidative stress levels during osteoclast differentiation. At the molecular level, the 1-2 T SMF combined with IONPs inhibits the expression of the NF- $\kappa$ B and MAPK signaling pathways (Zhang *et al.*, 2022). Meanwhile, the appropriate ratio of Fe/Ca = 1:15, mol/mol (SPIO@15HA) inhibited the formation of osteoclasts through the TRAF6-p62-CYLD pathway. Besides, the osteogenic differentiation process was enhanced by the regulation of TGF- $\beta$ , PI3K-AKT, and calcium signaling pathways. Furthermore, the overexpressed cytokines such as OPG, CSF2, and CCL2 also contributed to the maintenance of bone remodeling balance (Li *et al.*, 2021). The senescence-associated secretory phenotype of immune cells and bone-related cells is widely recognized as an important source of inflammatory cytokines that contribute greatly to the progression of OP. Whether IONPs have a regulatory effect on the production of inflammation still needs to be explored.

### Application of IONPs in Intervertebral Disc Diseases


The intervertebral disc is another site that is linked to orthopaedic degenerative diseases and is also a leading cause of disability in elderly individuals, and the common clinical manifestation is low back pain (Xin *et al.*, 2022). The exploration of IONPs in intervertebral discs

has focused mainly on diagnosis or combination with stem cell therapy for IDD. For example, Guillaume Bierry *et al.* (2009) used IONP-enhanced MRI to identify infectious and degenerative vertebral disorders, which could distinguish between the two diseases according to the quantitative results. In other studies, IONPs were used to mark MSCs to evaluate their survival and differentiation (Handley *et al.*, 2015; Hang *et al.*, 2017; Saldanha *et al.*, 2008). Additionally, recent research has used IONPs as a magnetofection system to deliver miR-21 into stem cells for intervertebral fusion operations, which is the only therapeutic application of IONPs in IDD (Wang *et al.*, 2023a). Studies have shown that inflammation, mitochondrial DNA damage and apoptosis play an important role in the pathological process of intervertebral disc cell degeneration (Zhou *et al.*, 2024). Silence-activated transcription factor 3 (ATF3) blocks the pathological process of IVDD by regulating iron apoptosis, apoptosis, inflammation, and extracellular matrix (ECM) metabolism in nucleus pulposus cells (NPCs) (Wang *et al.*, 2024c). Sirtuins/SIRT1s and their related activators regulate autophagy, myeloid apoptosis, oxidative stress and extracellular matrix degradation, and have positive effects on the treatment of IVDD (Shen *et al.*, 2024). Prolonged exposure to high concentrations of IONPs may induce oxidative stress and inflammatory translation (Vidya Balakrishnan *et al.*, 2024), but there is insufficient evidence of IONPs and inflammatory response in the treatment and imaging of IDD. Overall, the application of IONPs for treating degenerative diseases of the spine is still in the initial stages. Based on the similar pathogenesis of IDD and OA, future work on the spine is warranted.

### Discussion

In the field of biomaterials, nanoparticles have been widely applied due to their unique physicochemical properties (Zheng *et al.*, 2024). These nanoparticles can be widely used for diagnosing, treating and preventing orthopaedic diseases. Herein, we chose IONPs as representative nanoparticles and summarized their application



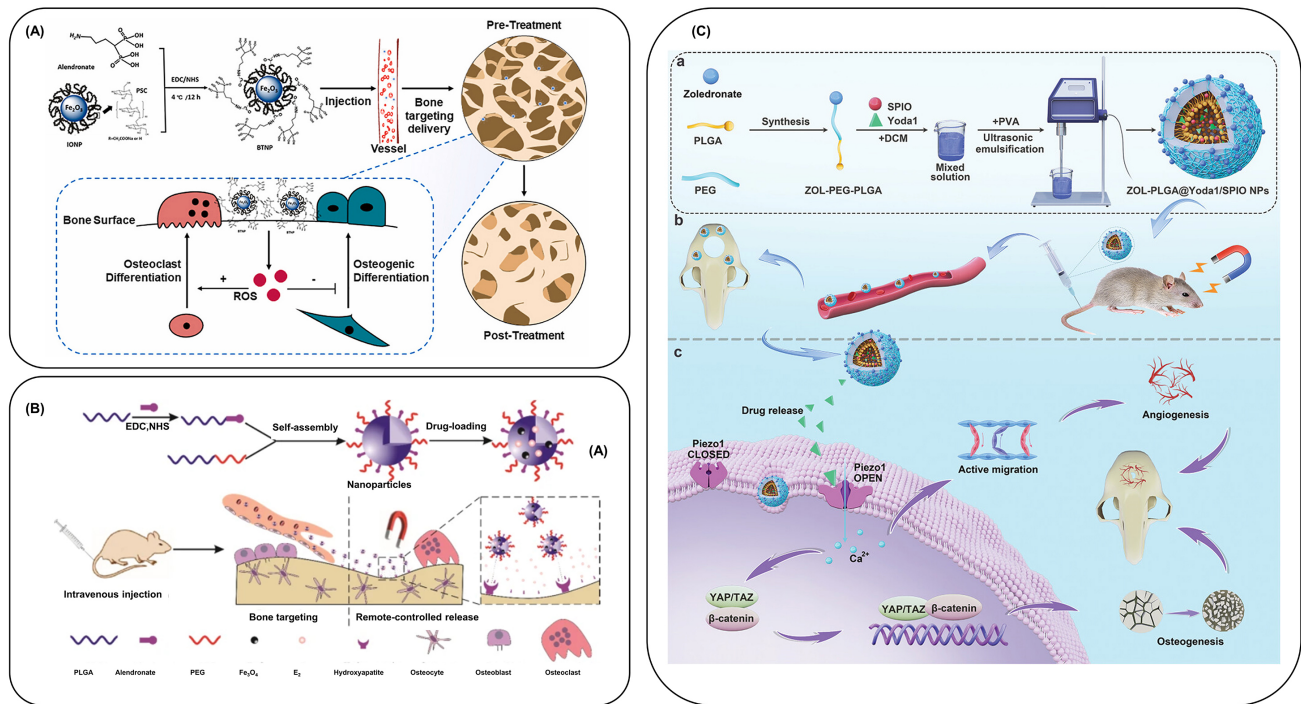

**Fig. 4. Modified IONPs for treating osteoporosis.** (A) Bone-targeting IONPs for treating postmenopausal osteoporosis; images were obtained from Zheng *et al.*, (2022). (B) Bone-targeting IONPs combined with estradiol for treating postmenopausal osteoporosis; images were obtained from Guo *et al.*, (2021). (C) Bone-targeting IONPs combined with Yoda1 for treating osteoporosis, images were obtained from Guan *et al.*, (2023). Abbreviations: EDC, 1-Ethyl-3-(3-dimethylaminopropyl) carbodiimide; NHS, N-hydroxysuccinimide.

in the orthopaedic field. Compared with other types of nanoparticles, IONPs have the unique advantage of magnetic properties and are also an important trace element in the human body. Iron metabolism in humans is a complex process involving duodenal enterocytes, plasma, erythroid bone marrow, the spleen, and the liver (Chifman *et al.*, 2014). Many degenerative diseases have been linked to ferroptosis, which is a unique type of cell death mediated by iron-dependent lipid superoxidation (Jiang *et al.*, 2021). Thus, the biosecurity of IONPs has been challenged. However, in our and others' previous work, suitable polymer coatings that can scavenge the existing ROS produced during ferroptosis can help to prevent iron accumulation-induced degenerative diseases (Guan *et al.*, 2023; Yu *et al.*, 2020; Zheng *et al.*, 2022). Recently, many biosynthetic polymers with antioxidant activity, such as lignin, chitosan, and functional liposomes, have been identified (Pei *et al.*, 2023; Zheng *et al.*, 2021a; Zheng *et al.*, 2021b). Surprisingly, we also found that IONPs can prevent the senescent secretion phenotype (data not published), which means that the intracellular delivery of Fe<sup>2+</sup> might involve an independent pathway to improve the inflammatory microenvironment. The crosstalk between IONPs and the immune system is worth exploring.

In addition to their direct effects, the synergistic effects of IONPs with typical therapeutic methods attracted our attention. The most common application is the combination of IONPs with stem cells, in which the IONPs play

a multimodal role. In the process of clinical translation of stem cell therapy, the greatest obstacle is the risk of tumorigenicity, while the IONPs can act as surveillants. In preclinical and clinical experiments, IONPs can be used to collect data for the analysis of the proliferation and differentiation of stem cells. On the other hand, the IONPs could directly act on stem cells and regulate their behaviour, enhancing their ability to promote osteogenesis/chondrogenesis for tissue repair to treat degenerative orthopaedic diseases (Table 3). In addition to the advantage of integration of IONPs with stem cells, several distinct challenges still remained to be addressed. A major challenge lies in achieving high-efficiency labeling of stem cells with IONPs while maintaining cell viability and functionality (Berman *et al.*, 2011; Küstermann *et al.*, 2008; Lin *et al.*, 2017; Zheng *et al.*, 2016). It was reported that the surface modified IONPs performed better in the long-term tracing of stem cells, such as the application of glucosamine, self-assembled peptide amphiphile, high-molecular polymers, amine and silica (Guldris *et al.*, 2017; Yang *et al.*, 2016; Yao *et al.*, 2020; Liang *et al.*, 2023a, Liu *et al.*, 2020). Current methods often result in variable labeling efficiencies, which can limit the accuracy of tracking and monitoring stem cells, which could be improved by the development of device to generate focusing magnetic field and IONPs with more precise magnetic properties (Liu and Ho, 2017; Wang *et al.*, 2020; Wang *et al.*, 2022b). Furthermore, the translation of IONP-based stem cell therapies from the laboratory to clinical settings

**Table 3. The researches of the effect of IONPs on osteogenic differentiation.**

IONPs	Magnetic field intensity	Cell type	Animal model	Conclusions	Reference
Collagen–chitosan–hydroxyapatite–Fe <sub>2</sub> O <sub>3</sub>	250 mT	MG-63 osteoblast-like cells	None	Enhances ALP activity, osteocalcin synthesis and new bone tissue formation	(Paun <i>et al.</i> , 2018)
PLA-nHA-Fe <sub>2</sub> O <sub>3</sub>	0.05-25 mT	None	Rabbit model of lumbar transverse defects	Accelerates new bone tissue formation and remodelling <i>in vivo</i>	(Meng <i>et al.</i> , 2013)
ECM-RSF-Fe <sub>2</sub> O <sub>3</sub>	1 mT-1 T	Rat BMSCs	Critical-sized femur defect in a rat model	Enhances the osteogenic differentiation of BMSCs <i>in vitro</i> and new bone formation <i>in vivo</i>	(Liang <i>et al.</i> , 2023a)
R-IONPs-HA	Not clear	MC3T3-E1	None	Promotes proliferation and osteogenic differentiation	(Wang <i>et al.</i> , 2021a)
Fe-HA	320 mT	Saos-2 human osteoblast-like cells	A rabbit critical bone defect model	Promotes cell proliferation and osteoblast activity <i>in vivo</i>	(Panseri <i>et al.</i> , 2012)
APTES-nHAp-IONPs	Not clear	MC3T3-E1 and 4B12	None	Enhances the metabolic activity of osteoblasts and diminishes osteoclasts' metabolism	(Marycz <i>et al.</i> , 2022)
IONP-CPC	Not clear	hDPSCs	Subcutaneous implantation in mice	Enhances ALP activity and bone mineral synthesis <i>in vitro</i> and enhances osteogenesis <i>in vivo</i>	(Xia <i>et al.</i> , 2019b)
Silk fibroin–hydroxyapatite–IONPs	Not clear	BMSCs	Subcutaneous implantation in mice	Promotes cell adhesion, growth, and osteogenesis <i>in vitro</i> and facilitates bone formation <i>in vivo</i>	(Liu <i>et al.</i> , 2020)

faces numerous hurdles, including concerns regarding biocompatibility, long-term safety, and regulatory approval.

IONPs exhibit significant potential when integrated with drugs, genes, and biomaterials to form multifunctional nanoplatforms aimed at synergistic therapeutic outcomes. As drug carriers, IONPs facilitate precise delivery via magnetic targeting, enhancing bioavailability and therapeutic efficacy. They also function as sustained-release agents, extending drug release and therapeutic duration (Tran *et al.*, 2022). The multifunctional hybrids are used to treat cancers and achieved a lot of success (Ghadimi Darsajini *et al.*, 2023; Feng *et al.*, 2023; Hasani *et al.*, 2023; Wang *et al.*, 2023b). However, in the orthopedic field, the application of multifunctional IONPs containing hybrids in diagnosing and treating diseases is still in the early stage. Previously, the combination application of IONPs with different drugs, such as salicylic acid, dexamethasone, folic acid, alendronate, and exosomes were proven efficient in treating OA and OP (Ibrahiem *et al.*, 2023; Marycz *et al.*, 2020; Shah *et al.*, 2017; Tran *et al.*, 2022, Marycz *et al.*, 2022, Meng *et al.*, 2013). However, current work are more likely to use the IONPs as a drug which can synergetically

perform therapeutic effect with the typical drugs. As we previous reported, the multifunctional nanoplatforms can be obtained as two styles: the multifunction of one single functional unit, and the combination of different functional units (Zheng *et al.*, 2024). Due to the complex structure and physicochemical properties, IONPs are easily to be used as therapeutic core and nano-vechiles which is easily to be translated to treat diseases with different pathologies, such as OA. However, various factors, such as charge, particle size, and surface modifications, influence the nanoplatform preparation methods based on IONPs. Also, drug-IONPs integration may alter physicochemical properties, affecting stability and bioactivity. The integration process requires careful consideration of compatibility, stability, biological activity, and safety of the nanoplatforms.

In conclusion, IONPs are novel nanoagents that could be translated to the clinic for the treatment and diagnosis of orthopaedic degenerative diseases. However, some unsolved questions worth studying persist, such as the improvement of biosecurity and potential molecular mechanisms involved in regulating cellular behaviours. After these obstacles are solved, more clinical trials are needed

in the future.

## List of Abbreviations

ACI, autologous chondrocyte implantation; ADSCs, adipose-derived stem cells; ATF3, activated transcription factor 3; BMSCs, bone mesenchymal stem cells; CPC, calcium phosphate cement; ECM, extracellular matrix; EDC, 1-Ethyl-3-(3-dimethylaminopropyl)carbodiimide; HBM-SCs, human bone marrow stromal cells; IDD, intervertebral disc disease; IONPs, iron oxide nanoparticles; MPI, magnetic particle imaging; MR, Magnetic Resonance; MSCs, mesenchymal stem cells; NHS, N-hydroxysuccinimide; NPC, nucleus pulposus cell; NSAIDs, nonsteroidal anti-inflammatory drugs; OP, osteoporosis; OA, osteoarthritis; RES, reticuloendothelial system; ROS, reactive oxygen species; SMF, static magnetic field; SPIONs, superparamagnetic iron oxide nanoparticles.

## Availability of Data and Materials

Not applicable.

## Author Contributions

Conceptualization: XLZ, LFJ, LMZ. Methodology: XLZ, QCF, LMZ. Investigation: XLZ, QCF. Visualization: XLZ, QCF, LMZ. Supervision: LFJ, and LMZ. Writing—original draft: XLZ, and QCF. Writing—review and editing: LFJ, LMZ. All authors contributed to editorial changes in the manuscript. All authors read and approved the final manuscript. All authors have participated sufficiently in the work and agreed to be accountable for all aspects of the work.

## Ethics Approval and Consent to Participate

Not applicable.

## Acknowledgments

Not applicable.

## Funding

This research was supported by Basic Public Welfare Research Project of Zhejiang Province (Grant no. LY22H180004); China Postdoctoral Foundation under Grant Number 2022M722769 and 2024T170775.

## Conflict of Interest

The authors declare no conflict of interest.

## References

Abakumov MA, Semkina AS, Skorikov AS, Vishnevskiy DA, Ivanova AV, Mironova E, Davydova GA, Majouga AG, Chekhonin VP (2018) Toxicity of iron oxide nanoparticles: Size and coating effects. *Journal of Biochemical and Molecular Toxicology* 32: e22225. DOI: 10.1002/jbt.22225.

Abbas H, Gad HA, El Sayed NS, Rashed LA, Khattab MA, Noor AO, Zewail M (2022a) Development and Evaluation of Novel Leflunomide SPION Bioemulsomes for the Intra-Articular Treatment of Arthritis. *Pharmaceutics* 14: 2005. DOI: 10.3390/pharmaceutics14102005.

Abbas H, El Sayed NS, Ali ME, Elsheikh MA (2022b) Integrated lecithin-bile salt nanovesicles as a promising approach for effective skin delivery of luteolin to improve UV-induced skin damage in Wistar Albino rats. *Colloids and Surfaces. B, Biointerfaces* 211: 112299. DOI: 10.1016/j.colsurfb.2021.112299.

Abdelbari MA, El-Gazar AA, Abdelbary AA, Elshafeey AH, Mosallam S (2023) Brij® integrated bilosomes for improving the transdermal delivery of niflumic acid for effective treatment of osteoarthritis: In vitro characterization, ex vivo permeability assessment, and in vivo study. *International Journal of Pharmaceutics* 640: 123024. DOI: 10.1016/j.ijpharm.2023.123024.

Agrawal AC, Garg AK (2023) Epidemiology of Osteoporosis. *Indian Journal of Orthopaedics* 57: 45-48. DOI: 10.1007/s43465-023-01012-3.

Ajayi TO, Liu S, Rosen C, Rinaldi-Ramos CM, Allen KD, Sharma B (2023) Application of magnetic particle imaging to evaluate nanoparticle fate in rodent joints. *Journal of Controlled Release: Official Journal of the Controlled Release Society* 356: 347-359. DOI: 10.1016/j.jconrel.2023.02.038.

Ali A, Zafar H, Zia M, Ul Haq I, Phull AR, Ali JS, Hussain A (2016) Synthesis, characterization, applications, and challenges of iron oxide nanoparticles. *Nanotechnology, Science and Applications* 9: 49-67. DOI: 10.2147/NSA.S99986.

Allen KD, Thoma LM, Golightly YM (2022) Epidemiology of osteoarthritis. *Osteoarthritis and Cartilage* 30: 184-195. DOI: 10.1016/j.joca.2021.04.020.

Anjum S, Arya DK, Saeed M, Ali D, Athar MS, Yulin W, Alarifi S, Wu X, Rajinikanth PS, Ao Q (2023) Multifunctional electrospun nanofibrous scaffold enriched with alendronate and hydroxyapatite for balancing osteogenic and osteoclast activity to promote bone regeneration. *Frontiers in Bioengineering and Biotechnology* 11: 1302594. DOI: 10.3389/fbioe.2023.1302594.

Aouad D, Azar N, Daher M, Dib N, El Rassi G (2023) Untreated Atypical Left Femoral Shaft Fracture: A Case Report of Its Complication. *International Journal of Clinical Research* 3: 212-218. DOI: 10.38179/ijcr.v3i1.159.

Bartkowski M, Zhou Y, Nabil Amin Mustafa M, Eustace AJ, Giordani S (2024) CARBON DOTS: Bioimaging and Anticancer Drug Delivery. *Chemistry (Weinheim an Der Bergstrasse, Germany)* 30: e202303982. DOI: 10.1002/chem.202303982.

Berman SC, Galpoththawela C, Gilad AA, Bulte JWM, Walczak P (2011) Long-term MR cell tracking of neural stem cells grafted in immunocompetent versus immunodeficient mice reveals distinct differences in con-

trast between live and dead cells. *Magnetic Resonance in Medicine* 65: 564-574. DOI: [10.1002/mrm.22613](https://doi.org/10.1002/mrm.22613).

Bierry G, Jehl F, Holl N, Sibilia J, Froelich S, Froehlig P, Diemann JL, Kremer S (2009) Cellular magnetic resonance imaging for the differentiation of infectious and degenerative vertebral disorders: preliminary results. *Journal of Magnetic Resonance Imaging: JMRI* 30: 901-906. DOI: [10.1002/jmri.21904](https://doi.org/10.1002/jmri.21904).

Black DM, Geiger EJ, Eastell R, Vittinghoff E, Li BH, Ryan DS, Dell RM, Adams AL (2020) Atypical Femur Fracture Risk versus Fragility Fracture Prevention with Bisphosphonates. *The New England Journal of Medicine* 383: 743-753. DOI: [10.1056/NEJMoa1916525](https://doi.org/10.1056/NEJMoa1916525).

Bullock J, Rizvi SAA, Saleh AM, Ahmed SS, Do DP, Ansari RA, Ahmed J (2018) Rheumatoid Arthritis: A Brief Overview of the Treatment. *Medical Principles and Practice: International Journal of the Kuwait University, Health Science Centre* 27: 501-507. DOI: [10.1159/000493390](https://doi.org/10.1159/000493390).

Bulte JWM, Walczak P, Janowski M, Krishnan KM, Arami H, Halkola A, Gleich B, Rahmer J (2015) Quantitative “Hot Spot” Imaging of Transplanted Stem Cells using Superparamagnetic Tracers and Magnetic Particle Imaging (MPI). *Tomography (Ann Arbor, Mich.)* 1: 91-97. DOI: [10.18383/j.tom.2015.00172](https://doi.org/10.18383/j.tom.2015.00172).

Butoescu N, Seemayer CA, Foti M, Jordan O, Doelker E (2009) Dexamethasone-containing PLGA superparamagnetic microparticles as carriers for the local treatment of arthritis. *Biomaterials* 30: 1772-1780. DOI: [10.1016/j.biomaterials.2008.12.017](https://doi.org/10.1016/j.biomaterials.2008.12.017).

Cao W, Sun M, Yu KN, Zhao L, Feng Y, Tan C, Yang M, Wang Y, Zhu F, Chen L, Nie L, Zhao Y, Chen G, Han W (2024) Exogenous carbon monoxide promotes GPX4-dependent ferroptosis through ROS/GSK3 $\beta$  axis in non-small cell lung cancer. *Cell Death Discovery* 10: 42. DOI: [10.1038/s41420-023-01743-0](https://doi.org/10.1038/s41420-023-01743-0).

Chang D, Ma Y, Xu X, Xie J, Ju S (2021) Stimuli-Responsive Polymeric Nanoplatforams for Cancer Therapy. *Frontiers in Bioengineering and Biotechnology* 9: 707319. DOI: [10.3389/fbioe.2021.707319](https://doi.org/10.3389/fbioe.2021.707319).

Chaudhari D, Panda G (2023) A brief overview on iron oxide nanoparticle synthesis, characterization, and applications. *Materials Today: Proceedings*. DOI: [10.1016/j.matpr.2023.10.087](https://doi.org/10.1016/j.matpr.2023.10.087).

Chen KJ, Wolahan SM, Wang H, Hsu CH, Chang HW, Durazo A, Hwang LP, Garcia MA, Jiang ZK, Wu L, Lin YY, Tseng HR (2011) A small MRI contrast agent library of gadolinium(III)-encapsulated supramolecular nanoparticles for improved relaxivity and sensitivity. *Biomaterials* 32: 2160-2165. DOI: [10.1016/j.biomaterials.2010.11.043](https://doi.org/10.1016/j.biomaterials.2010.11.043).

Chifman J, Laubenbacher R, Torti SV (2014) A systems biology approach to iron metabolism. *Advances in Experimental Medicine and Biology* 844: 201-225. DOI: [10.1007/978-1-4939-2095-2\\_10](https://doi.org/10.1007/978-1-4939-2095-2_10).

Choi HS, Liu W, Misra P, Tanaka E, Zimmer JP, Ito Ipe B, Bawendi MG, Frangioni JV (2007) Renal clearance

of quantum dots. *Nature Biotechnology* 25: 1165-1170. DOI: [10.1038/nbt1340](https://doi.org/10.1038/nbt1340).

Compston JE, McClung MR, Leslie WD (2019) Osteoporosis. *Lancet (London, England)* 393: 364-376. DOI: [10.1016/S0140-6736\(18\)32112-3](https://doi.org/10.1016/S0140-6736(18)32112-3).

Coradduzza D, Congiargiu A, Chen Z, Zinellu A, Carru C, Medici S (2023) Ferroptosis and Senescence: A Systematic Review. *International Journal of Molecular Sciences* 24: 3658. DOI: [10.3390/ijms24043658](https://doi.org/10.3390/ijms24043658).

Dadfar SM, Roemhild K, Drude NI, von Stillfried S, Knüchel R, Kiessling F, Lammers T (2019) Iron oxide nanoparticles: Diagnostic, therapeutic and theranostic applications. *Advanced Drug Delivery Reviews* 138: 302-325. DOI: [10.1016/j.addr.2019.01.005](https://doi.org/10.1016/j.addr.2019.01.005).

Darmawan A, Smart S, Julbe A, Diniz da Costa JC (2010) Iron Oxide Silica Derived from Sol-Gel Synthesis. *Materials (Basel, Switzerland)* 4: 448-456. DOI: [10.3390/ma4020448](https://doi.org/10.3390/ma4020448).

Das B, Girigoswami A, Dutta A, Pal P, Dutta J, Dadhich P, Srivas PK, Dhara S (2019) Carbon Nanodots Doped Super-paramagnetic Iron Oxide Nanoparticles for Multimodal Bioimaging and Osteochondral Tissue Regeneration via External Magnetic Actuation. *ACS Biomaterials Science & Engineering* 5: 3549-3560. DOI: [10.1021/acsbio-materials.9b00571](https://doi.org/10.1021/acsbio-materials.9b00571).

Del Bianco L, Spizzo F, Yang Y, Greco G, Gatto ML, Barucca G, Pugno NM, Motta A (2022) Silk fibroin films with embedded magnetic nanoparticles: evaluation of the magneto-mechanical stimulation effect on osteogenic differentiation of stem cells. *Nanoscale* 14: 14558-14574. DOI: [10.1039/d2nr03167a](https://doi.org/10.1039/d2nr03167a).

Di Marco A, Anguera I, Schmitt M, Klem I, Neilan TG, White JA, Sramko M, Masci PG, Barison A, Mckenna P, Mordi I, Haugaa KH, Leyva F, Rodriguez Capitán J, Satoh H, Nabeta T, Dallaglio PD, Campbell NG, Sabaté X, Cequier Á (2017) Late Gadolinium Enhancement and the Risk for Ventricular Arrhythmias or Sudden Death in Dilated Cardiomyopathy: Systematic Review and Meta-Analysis. *JACC. Heart Failure* 5: 28-38. DOI: [10.1016/j.jchf.2016.09.017](https://doi.org/10.1016/j.jchf.2016.09.017).

Eckstein F, Cicuttini F, Raynauld JP, Waterton JC, Peterfy C (2006) Magnetic resonance imaging (MRI) of articular cartilage in knee osteoarthritis (OA): morphological assessment. *Osteoarthritis and Cartilage* 14 Suppl A: A46-75. DOI: [10.1016/j.joca.2006.02.026](https://doi.org/10.1016/j.joca.2006.02.026).

Endale HT, Tesfaye W, Mengstie TA (2023) ROS induced lipid peroxidation and their role in ferroptosis. *Frontiers in Cell and Developmental Biology* 11: 1226044. DOI: [10.3389/fcell.2023.1226044](https://doi.org/10.3389/fcell.2023.1226044).

Ensrud KE, Crandall CJ (2024) Osteoporosis. *Annals of Internal Medicine* 177: ITC1-ITC16. DOI: [10.7326/AITC202401160](https://doi.org/10.7326/AITC202401160).

Fan L, Du P, Li Y, Chen X, Liu F, Liu Y, Petrov AM, Li X, Wang Z, Zhao Y (2024) Targeted Liposomes Sensitize Plastic Melanoma to Ferroptosis via Senescence Induction

and Coenzyme Depletion. *ACS Nano* 18: 7011-7023. DOI: 10.1021/acsnano.3c10142.

Feng K, Xu Z, Wang Y, Wu X, Xiong F, Ruan Y, Wu X, Ye L, Su D, Yu J, Sun X (2023) Renal-clearable porous hollow copper iron oxide nanoparticles for trimodal chemodynamic-photothermal-chemo anti-tumor therapy. *Nanoscale* 15: 3188-3198. DOI: 10.1039/d2nr06224k.

Fouad-Elhady EA, Aglan HA, Hassan RE, Ahmed HH, Sabry GM (2020) Modulation of bone turnover aberration: A target for management of primary osteoporosis in experimental rat model. *Heliyon* 6: e03341. DOI: 10.1016/j.heliyon.2020.e03341.

Garraud A, Velez C, Shah Y, Garraud N, Kozissnik B, Yarmola EG, Allen KD, Dobson J, Arnold DP (2016) Investigation of the Capture of Magnetic Particles from High-Viscosity Fluids Using Permanent Magnets. *IEEE Transactions on Bio-medical Engineering* 63: 372-378. DOI: 10.1109/TBME.2015.2458783.

Ghadimi Darsajini A, Soleimani M, Mirjani R (2023) The Combination of Photothermal Therapy and Chemotherapy using Alginate-Modified Iron Oxide-Gold Nanohybrids Carrying Cisplatin. *Journal of Biomedical Physics & Engineering* 13: 117-124. DOI: 10.31661/jbpe.v0i0.2003-1083.

Gong X, Wang F, Huang Y, Lin X, Chen C, Wang F, Yang L (2018) Magnetic-targeting of polyethylenimine-wrapped iron oxide nanoparticle labeled chondrocytes in a rabbit articular cartilage defect model. *RSC Advances* 8: 7633-7640. DOI: 10.1039/c7ra12039g.

Graeser M, Thieben F, Szwargulski P, Werner F, Gdaniec N, Boberg M, Griese F, Möddel M, Ludewig P, van de Ven D, Weber OM, Woywode O, Gleich B, Knopp T (2019) Human-sized magnetic particle imaging for brain applications. *Nature Communications* 10: 1936. DOI: 10.1038/s41467-019-09704-x.

Gu H, Fu S, Cai Z, Ai H (2024) Polymer/iron oxide nanocomposites as magnetic resonance imaging contrast agents: Polymer modulation and probe property control. *Journal of Polymer Science*. DOI: 10.1002/pol.20230820.

Guan H, Wang W, Jiang Z, Zhang B, Ye Z, Zheng J, Chen W, Liao Y, Zhang Y (2023) Magnetic Aggregation-Induced Bone-Targeting Nanocarrier with Effects of Piezo1 Activation and Osteogenic-Angiogenic Coupling for Osteoporotic Bone Repair. *Advanced Materials (Deerfield Beach, Fla.)* 36: e2312081. DOI: 10.1002/adma.202312081.

Guldris N, Argibay B, Gallo J, Iglesias-Rey R, Carbó-Argibay E, Kolen'ko YV, Campos F, Sobrino T, Salonen LM, Bañobre-López M, Castillo J, Rivas J (2017) Magnetite Nanoparticles for Stem Cell Labeling with High Efficiency and Long-Term in Vivo Tracking. *Bioconjugate Chemistry* 28: 362-370. DOI: 10.1021/acs.bioconjchem.6b00522.

Guo J, Xu L, Zhang H, Yang Q (2020) Clinical Analysis of Magnetic Nanoparticle Contrast Agent in the Diag-

nosis of Occult Fracture by Multislice Spiral CT and MRI. *Journal of Nanoscience and Nanotechnology* 20: 6568-6576. DOI: 10.1166/jnn.2020.18565.

Guo Y, Liu Y, Shi C, Wu T, Cui Y, Wang S, Liu P, Feng X, He Y, Fu D (2021) Remote-controllable bone-targeted delivery of estradiol for the treatment of ovariectomy-induced osteoporosis in rats. *Journal of Nanobiotechnology* 19: 248. DOI: 10.1186/s12951-021-00976-4.

Gupta AK, Gupta M (2005) Synthesis and surface engineering of iron oxide nanoparticles for biomedical applications. *Biomaterials* 26: 3995-4021. DOI: 10.1016/j.biomaterials.2004.10.012.

Hamad MA, Alamri HR, Harb ME (2021) Environmentally Friendly Energy Harvesting Using Magnetocaloric Solid-State Nanoparticles as Magnetic Refrigerator. *Journal of Low Temperature Physics* 204: 57-63. DOI: 10.1007/s10909-021-02595-7.

Handley C, Goldschlager T, Oehme D, Ghosh P, Jenkin G (2015) Mesenchymal stem cell tracking in the intervertebral disc. *World Journal of Stem Cells* 7: 65-74. DOI: 10.4252/wjsc.v7.i1.65.

Hang D, Li F, Che W, Wu X, Wan Y, Wang J, Zheng Y (2017) One-Stage Positron Emission Tomography and Magnetic Resonance Imaging to Assess Mesenchymal Stem Cell Survival in a Canine Model of Intervertebral Disc Degeneration. *Stem Cells and Development* 26: 1334-1343. DOI: 10.1089/scd.2017.0103.

Hang J, Guo Z, Zhong C, Sun A, He K, Liu X, Song H, Li J (2024) A super magnetic porous biochar manufactured by potassium ferrate-accelerated hydrothermal carbonization for removal of tetracycline. *Journal of Cleaner Production* 435: 140470. DOI: 10.1016/j.jclepro.2023.140470.

Harris RA, Shumbula PM, van der Walt H (2015) Analysis of the interaction of surfactants oleic acid and oleylamine with iron oxide nanoparticles through molecular mechanics modeling. *Langmuir: the ACS Journal of Surfaces and Colloids* 31: 3934-3943. DOI: 10.1021/acs.langmuir.5b00671.

Hasani M, Jafari S, Akbari Javar H, Abdollahi H, Rashidzadeh H (2023) Cell-Penetrating Peptidic GRP78 Ligand-Conjugated Iron Oxide Magnetic Nanoparticles for Tumor-Targeted Doxorubicin Delivery and Imaging. *ACS Applied Bio Materials* 6: 1019-1031. DOI: 10.1021/ac-sabm.2c00897.

Hedvičáková V, Žižková R, Buzgo M, Vištejnová L, Klein P, Hovořáková M, Bartoš M, Steklíková K, Luňáčková J, Šebová E, Paurová I, Rysová M, Filová E, Rampichová M (2023) The Gradual Release of Alendronate for the Treatment of Critical Bone Defects in Osteoporotic and Control Rats. *International Journal of Nanomedicine* 18: 541-560. DOI: 10.2147/IJN.S386784.

Huang J, Liu W, Liang Y, Li L, Duan L, Chen J, Zhu F, Lai Y, Zhu W, You W, Jia Z, Xiong J, Wang D (2018) Preparation and biocompatibility of diphasic mag-

netic nanocomposite scaffold. *Materials Science & Engineering. C, Materials for Biological Applications* 87: 70-77. DOI: [10.1016/j.msec.2018.02.003](https://doi.org/10.1016/j.msec.2018.02.003).

Hufschmid R, Arami H, Ferguson RM, Gonzales M, Teeman E, Brush LN, Browning ND, Krishnan KM (2015) Synthesis of phase-pure and monodisperse iron oxide nanoparticles by thermal decomposition. *Nanoscale* 7: 11142-11154. DOI: [10.1039/c5nr01651g](https://doi.org/10.1039/c5nr01651g).

Hussain SM, Hess KL, Gearhart JM, Geiss KT, Schlager JJ (2005) In vitro toxicity of nanoparticles in BRL 3A rat liver cells. *Toxicology in Vitro: an International Journal Published in Association with BIBRA* 19: 975-983. DOI: [10.1016/j.tiv.2005.06.034](https://doi.org/10.1016/j.tiv.2005.06.034).

Hwang ET (2024) Robust enzyme-iron oxide nanoparticle composites entrapped in mesoporous silica nanospheres and their properties. *LWT* 197: 115900. DOI: [10.1016/j.lwt.2024.115900](https://doi.org/10.1016/j.lwt.2024.115900).

Ibrahiem B, Shamma R, Salama A, Refai H (2023) Magnetic targeting of lornoxicam/SPION bilosomes loaded in a thermosensitive in situ hydrogel system for the management of osteoarthritis: Optimization, in vitro, ex vivo, and in vivo studies in rat model via modulation of RANKL/OPG. *Drug Delivery and Translational Research* 14: 1982-2002. DOI: [10.1007/s13346-023-01503-8](https://doi.org/10.1007/s13346-023-01503-8).

Israel LL, Galstyan A, Holler E, Ljubimova JY (2020) Magnetic iron oxide nanoparticles for imaging, targeting and treatment of primary and metastatic tumors of the brain. *Journal of Controlled Release: Official Journal of the Controlled Release Society* 320: 45-62. DOI: [10.1016/j.jconrel.2020.01.009](https://doi.org/10.1016/j.jconrel.2020.01.009).

Jeng HA, Swanson J (2006) Toxicity of metal oxide nanoparticles in mammalian cells. *Journal of Environmental Science and Health. Part A, Toxic/hazardous Substances & Environmental Engineering* 41: 2699-2711. DOI: [10.1080/10934520600966177](https://doi.org/10.1080/10934520600966177).

Jia Y, Zhang P, Sun Y, Kang Q, Xu J, Zhang C, Chai Y (2019) Regeneration of large bone defects using mesoporous silica coated magnetic nanoparticles during distraction osteogenesis. *Nanomedicine: Nanotechnology, Biology, and Medicine* 21: 102040. DOI: [10.1016/j.nano.2019.102040](https://doi.org/10.1016/j.nano.2019.102040).

Jiang F, Xiao JJ, Lu YT, Li W, Duan YW, Sheng ZH, Li SL (2017) Effect of superparamagnetic iron oxide on differentiation of rat bone marrow stem cells into chondrocytes in vitro. *Nan Fang Yi Ke Da Xue Xue Bao* 37: 652-658. DOI: [10.3969/j.issn.1673-4254.2017.05.14](https://doi.org/10.3969/j.issn.1673-4254.2017.05.14). (In Chinese)

Jiang X, Stockwell BR, Conrad M (2021) Ferroptosis: mechanisms, biology and role in disease. *Nature Reviews. Molecular Cell Biology* 22: 266-282. DOI: [10.1038/s41580-020-00324-8](https://doi.org/10.1038/s41580-020-00324-8).

Kamei N, Ochi M, Adachi N, Ishikawa M, Yanada S, Levin LS, Kamei G, Kobayashi T (2018) The safety and efficacy of magnetic targeting using autologous mesenchymal stem cells for cartilage repair. *Knee Surgery, Sports Traumatology, Arthroscopy: Official Journal of the ES-*

*SKA* 26: 3626-3635. DOI: [10.1007/s00167-018-4898-2](https://doi.org/10.1007/s00167-018-4898-2).

Kang ML, Ko JY, Kim JE, Im GI (2014) Intra-articular delivery of kartogenin-conjugated chitosan nano/microparticles for cartilage regeneration. *Biomaterials* 35: 9984-9994. DOI: [10.1016/j.biomaterials.2014.08.042](https://doi.org/10.1016/j.biomaterials.2014.08.042).

Karlsson HL, Cronholm P, Gustafsson J, Möller L (2008) Copper oxide nanoparticles are highly toxic: a comparison between metal oxide nanoparticles and carbon nanotubes. *Chemical Research in Toxicology* 21: 1726-1732. DOI: [10.1021/tx800064j](https://doi.org/10.1021/tx800064j).

Karlsson HL, Gustafsson J, Cronholm P, Möller L (2009) Size-dependent toxicity of metal oxide particles—a comparison between nano- and micrometer size. *Toxicology Letters* 188: 112-118. DOI: [10.1016/j.toxlet.2009.03.014](https://doi.org/10.1016/j.toxlet.2009.03.014).

Kim SE, Tieu MV, Hwang SY, Lee MH (2020) Magnetic Particles: Their Applications from Sample Preparations to Biosensing Platforms. *Micromachines* 11: 302. DOI: [10.3390/mi11030302](https://doi.org/10.3390/mi11030302).

Kobayashi T, Ochi M, Yanada S, Ishikawa M, Adachi N, Deie M, Arihiro K (2008) A novel cell delivery system using magnetically labeled mesenchymal stem cells and an external magnetic device for clinical cartilage repair. *Arthroscopy: the Journal of Arthroscopic & Related Surgery: Official Publication of the Arthroscopy Association of North America and the International Arthroscopy Association* 24: 69-76. DOI: [10.1016/j.arthro.2007.08.017](https://doi.org/10.1016/j.arthro.2007.08.017).

Kolecka MA, Arnhold S, Schmidt M, Reich C, Kramer M, Failing K, Pückler K (2017). Behaviour of adipose-derived canine mesenchymal stem cells after superparamagnetic iron oxide nanoparticles labelling for magnetic resonance imaging. *BMC veterinary research* 13: 62. DOI: [10.1186/s12917-017-0980-0](https://doi.org/10.1186/s12917-017-0980-0).

Kordoni M, Rigakos G, Kim YHM, Kaklamanis L, Nikolatou-Galitis O, Hadjiyassemi L, Labropoulos S, Razis E (2018) Atypical Femoral Fractures (AFF) from Bone Remodeling Agents in Patients with Cancer. *Anticancer Research* 38: 6439-6444. DOI: [10.21873/anticancer.13005](https://doi.org/10.21873/anticancer.13005).

Küstermann E, Himmelreich U, Kandal K, Geelen T, Ketkar A, Wiedermann D, Strecker C, Esser J, Arnhold S, Hoehn M (2008) Efficient stem cell labeling for MRI studies. *Contrast Media & Molecular Imaging* 3: 27-37. DOI: [10.1002/cmml.229](https://doi.org/10.1002/cmml.229).

Laurent S, Forge D, Port M, Roch A, Robic C, Vander Elst L, Muller RN (2008) Magnetic iron oxide nanoparticles: synthesis, stabilization, vectorization, physicochemical characterizations, and biological applications. *Chemical Reviews* 108: 2064-2110. DOI: [10.1021/cr068445e](https://doi.org/10.1021/cr068445e).

Lee MS, Su CM, Yeh JC, Wu PR, Tsai TY, Lou SL (2016) Synthesis of composite magnetic nanoparticles Fe<sub>3</sub>O<sub>4</sub> with alendronate for osteoporosis treatment. *International Journal of Nanomedicine* 11: 4583-4594. DOI: [10.2147/IJN.S112415](https://doi.org/10.2147/IJN.S112415).

- Li M, Fu S, Cai Z, Li D, Liu L, Deng D, Jin R, Ai H (2021) Dual regulation of osteoclastogenesis and osteogenesis for osteoporosis therapy by iron oxide hydroxyapatite core/shell nanocomposites. *Regenerative Biomaterials* 8: rbab027. DOI: 10.1093/rb/rbab027.
- Li S, Cao P, Chen T, Ding C (2023) Latest insights in disease-modifying osteoarthritis drugs development. *Therapeutic Advances in Musculoskeletal Disease* 15: 1759720X231169839. DOI: 10.1177/1759720X231169839.
- Liang HF, Zou YP, Hu AN, Wang B, Li J, Huang L, Chen WS, Su DH, Xiao L, Xiao Y, Ma YQ, Li XL, Jiang LB, Dong J (2023a) Biomimetic Structural Protein Based Magnetic Responsive Scaffold for Enhancing Bone Regeneration by Physical Stimulation on Intracellular Calcium Homeostasis. *Advanced Healthcare Materials* 12: e2301724. DOI: 10.1002/adhm.202301724.
- Liang W, Zhou C, Jin S, Fu L, Zhang H, Huang X, Long H, Ming W, Zhao J (2023b) An update on the advances in the field of nanostructured drug delivery systems for a variety of orthopedic applications. *Drug Delivery* 30: 2241667. DOI: 10.1080/10717544.2023.2241667.
- Liao SH, Liu CH, Bastakoti BP, Suzuki N, Chang Y, Yamauchi Y, Lin FH, Wu KCW (2015) Functionalized magnetic iron oxide/alginate core-shell nanoparticles for targeting hyperthermia. *International Journal of Nanomedicine* 10: 3315-3327. DOI: 10.2147/IJN.S68719.
- Lin BL, Zhang JZ, Lu LJ, Mao JJ, Cao MH, Mao XH, Zhang F, Duan XH, Zheng CS, Zhang LM, Shen J (2017) Superparamagnetic Iron Oxide Nanoparticles-Complexed Cationic Amylose for In Vivo Magnetic Resonance Imaging Tracking of Transplanted Stem Cells in Stroke. *Nanomaterials (Basel, Switzerland)* 7: 107. DOI: 10.3390/nano7050107.
- Ling D, Lee N, Hyeon T (2015) Chemical synthesis and assembly of uniformly sized iron oxide nanoparticles for medical applications. *Accounts of Chemical Research* 48: 1276-1285. DOI: 10.1021/acs.accounts.5b00038.
- Lisnyansky M, Kapelushnik N, Ben-Bassat A, Marom M, Loewenstein A, Khananshvili D, Giladi M, Haitin Y (2018) Reduced Activity of Geranylgeranyl Diphosphate Synthase Mutant Is Involved in Bisphosphonate-Induced Atypical Fractures. *Molecular Pharmacology* 94: 1391-1400. DOI: 10.1124/mol.118.113670.
- Liu J, Pearce CI, Liu C, Wang Z, Shi L, Arenholz E, Rosso KM (2013) Fe(3-x)Ti(x)O4 nanoparticles as tunable probes of microbial metal oxidation. *Journal of the American Chemical Society* 135: 8896-8907. DOI: 10.1021/ja4015343.
- Liu K, Zhang D, Wang W (2021) Nanoparticle-Based Drug Delivery System—A Target Strategy for Osteoarthritis Treatment. *Journal of Nanomaterials* 2021: 4064983. DOI: 10.1155/2021/4064983.
- Liu L, Ho C (2017) Mesenchymal Stem Cell Preparation and Transfection-free Ferumoxytol Labeling for MRI Cell Tracking. *Current Protocols in Stem Cell Biology* 43: 2B.7.1-2B.7.14. DOI: 10.1002/cpsc.38.
- Liu L, Jin R, Duan J, Yang L, Cai Z, Zhu W, Nie Y, He J, Xia C, Gong Q, Song B, Anderson JM, Ai H (2019) Bioactive iron oxide nanoparticles suppress osteoclastogenesis and ovariectomy-induced bone loss through regulating the TRAF6-p62-CYLD signaling complex. *Acta Biomaterialia* 103: 281-292. DOI: 10.1016/j.actbio.2019.12.022.
- Liu Q, Feng L, Chen Z, Lan Y, Liu Y, Li D, Yan C, Xu Y (2020) Ultrasmall Superparamagnetic Iron Oxide Labeled Silk Fibroin/Hydroxyapatite Multifunctional Scaffold Loaded With Bone Marrow-Derived Mesenchymal Stem Cells for Bone Regeneration. *Frontiers in Bioengineering and Biotechnology* 8: 697. DOI: 10.3389/fbioe.2020.00697.
- Liu Y, Jia S, Wu Q, Ran J, Zhang W, Wu S (2011) Studies of Fe3O4-chitosan nanoparticles prepared by coprecipitation under the magnetic field for lipase immobilization. *Catalysis Communications* 12: 717-720. DOI: 10.1016/j.catcom.2010.12.032.
- López-Sánchez J, Serrano A, del Campo A, Muñoz-Noval Á, Salas-Colera E, Cabero M, Varela M, Abuín M, Castro GR, Rubio-Zuazo J, Rodríguez de la Fuente Ó, Carmona N (2022) A combined micro-Raman, X-ray absorption and magnetic study to follow the glycerol-assisted growth of epsilon-iron oxide sol-gel coatings. *Journal of Alloys and Compounds* 892: 162061. DOI: 10.1016/j.jallcom.2021.162061.
- Ma X, Wang L, Wang P, Liu Z, Hao J, Wu J, Chu G, Huang M, Mair LO, Huang C, Xu T, Ying T, Tang X, Chen Y, Cai X, Zheng Y (2022) An electromagnetically actuated magneto-nanozyme mediated synergistic therapy for destruction and eradication of biofilm. *Chemical Engineering Journal* 431: 133971. DOI: 10.1016/j.cej.2021.133971.
- Makarczyk MJ, Gao Q, He Y, Li Z, Gold MS, Hochberg MC, Bunnell BA, Tuan RS, Goodman SB, Lin H (2021) Current Models for Development of Disease-Modifying Osteoarthritis Drugs. *Tissue Engineering. Part C, Methods* 27: 124-138. DOI: 10.1089/ten.TEC.2020.0309.
- Malehmir S, Esmaili MA, Khaksary Mahabady M, Sobhani-Nasab A, Atapour A, Ganjali MR, Ghasemi A, Moradi Hasan-Abad A (2023) A review: hemocompatibility of magnetic nanoparticles and their regenerative medicine, cancer therapy, drug delivery, and bioimaging applications. *Frontiers in Chemistry* 11: 1249134. DOI: 10.3389/fchem.2023.1249134.
- Malhotra N, Lee JS, Liman RAD, Ruallo JMS, Villaflores OB, Ger TR, Hsiao CD (2020) Potential Toxicity of Iron Oxide Magnetic Nanoparticles: A Review. *Molecules (Basel, Switzerland)* 25: 3159. DOI: 10.3390/molecules25143159.
- Marycz K, Kornicka-Garbowska K, Patej A, Sobierajska P, Kotela A, Turlej E, Kepska M, Bienko A, Wiglusz RJ (2022) Aminopropyltriethoxysilane (APTES)-

Modified Nanohydroxyapatite (nHAp) Incorporated with Iron Oxide (IO) Nanoparticles Promotes Early Osteogenesis, Reduces Inflammation and Inhibits Osteoclast Activity. *Materials (Basel, Switzerland)* 15: 2095. DOI: 10.3390/ma15062095.

Marycz K, Sobierajska P, Roecken M, Kornicka-Garbowska K, Kępska M, Idczak R, Nedelec JM, Wiglusz RJ (2020) Iron oxides nanoparticles (IOs) exposed to magnetic field promote expression of osteogenic markers in osteoblasts through integrin alpha-3 (INTa-3) activation, inhibits osteoclasts activity and exerts anti-inflammatory action. *Journal of Nanobiotechnology* 18: 33. DOI: 10.1186/s12951-020-00590-w.

Mei Z, Dhanale A, Gangaharan A, Sardar DK, Tang L (2016) Water dispersion of magnetic nanoparticles with selective Biofunctionality for enhanced plasmonic biosensing. *Talanta* 151: 23-29. DOI: 10.1016/j.talanta.2016.01.007.

Meng J, Xiao B, Zhang Y, Liu J, Xue H, Lei J, Kong H, Huang Y, Jin Z, Gu N, Xu H (2013) Super-paramagnetic responsive nanofibrous scaffolds under static magnetic field enhance osteogenesis for bone repair in vivo. *Scientific Reports* 3: 2655. DOI: 10.1038/srep02655.

Moacă EA, Watz C, Faur AC, Lazăr D, Socoliuc V, Păcurariu C, Ianoș R, Rus CI, Minda D, Barbu-Tudoran L, Dehelean CA (2023) Biologic Impact of Green Synthesized Magnetic Iron Oxide Nanoparticles on Two Different Lung Tumorigenic Monolayers and a 3D Normal Bronchial Model-EpiAirwayTM Microtissue. *Pharmaceutics* 15: 2. DOI: 10.3390/pharmaceutics15010002.

Mohamed S, Nasr M, Salama A, Refai H (2020) Novel lipid-polymer hybrid nanoparticles incorporated in thermosensitive in situ gel for intranasal delivery of terbutaline sulphate. *Journal of Microencapsulation* 37: 577-594. DOI: 10.1080/02652048.2020.1826590.

Morán D, Gutiérrez G, Mendoza R, Rayner M, Blanco-López C, Matos M (2023) Synthesis of controlled-size starch nanoparticles and superparamagnetic starch nanocomposites by microemulsion method. *Carbohydrate Polymers* 299: 120223. DOI: 10.1016/j.carbpol.2022.120223.

Mosallam S, Albash R, Abdelbari MA (2022) Advanced Vesicular Systems for Antifungal Drug Delivery. *AAPS PharmSciTech* 23: 206. DOI: 10.1208/s12249-022-02357-y.

Moseng T, Vliet Vlieland TPM, Battista S, Beckwée D, Boyadzhieva V, Conaghan PG, Costa D, Doherty M, Finney AG, Georgiev T, Gobbo M, Kennedy N, Kjekken I, Kroon FPB, Lohmander LS, Lund H, Mallen CD, Pavelka K, Pitsillidou IA, Rayman MP, Tveter AT, Vriezolk JE, Wiek D, Zanoli G, Østerås N (2024) EULAR recommendations for the non-pharmacological core management of hip and knee osteoarthritis: 2023 update. *Annals of the Rheumatic Diseases* 83: 730-740. DOI: 10.1136/ard-2023-225041.

Natarajan P, Tomich JM (2020) Understanding the influence of experimental factors on bio-interactions of nanoparticles: Towards improving correlation between in vitro and in vivo studies. *Archives of Biochemistry and Biophysics* 694: 108592. DOI: 10.1016/j.abb.2020.108592.

Ong YS, Bañobre-López M, Costa Lima SA, Reis S (2020) A multifunctional nanomedicine platform for co-delivery of methotrexate and mild hyperthermia towards breast cancer therapy. *Materials Science & Engineering. C, Materials for Biological Applications* 116: 111255. DOI: 10.1016/j.msec.2020.111255.

Paik SYR, Kim JS, Shin SJ, Ko S (2015) Characterization, Quantification, and Determination of the Toxicity of Iron Oxide Nanoparticles to the Bone Marrow Cells. *International Journal of Molecular Sciences* 16: 22243-22257. DOI: 10.3390/ijms160922243.

Panagiotopoulos N, Duschka RL, Ahlborg M, Bringout G, Debbeler C, Graeser M, Kaethner C, Lüdtke-Buzug K, Medimagh H, Stelzner J, Buzug TM, Barkhausen J, Vogt FM, Haegele J (2015) Magnetic particle imaging: current developments and future directions. *International Journal of Nanomedicine* 10: 3097-3114. DOI: 10.2147/IJN.S70488.

Panahifar A, Mahmoudi M, Doschak MR (2013) Synthesis and in vitro evaluation of bone-seeking superparamagnetic iron oxide nanoparticles as contrast agents for imaging bone metabolic activity. *ACS Applied Materials & Interfaces* 5: 5219-5226. DOI: 10.1021/am4010495.

Panda M, Bose A, Ganesan R, Ray Dutta J (2024) Polymerizable sol-gel synthesis of dark-visible light antibacterial magnetically-recoverable AgBr-loaded iron oxide/alumina nanocomposite. *Nanotechnology* 35: 10.1088/1361-6528/ad1056. DOI: 10.1088/1361-6528/ad1056.

Pang Y, Su L, Fu Y, Jia F, Zhang C, Cao X, He W, Kong X, Xu J, Zhao J, Qin A (2021) Inhibition of furin by bone targeting superparamagnetic iron oxide nanoparticles alleviated breast cancer bone metastasis. *Bioactive Materials* 6: 712-720. DOI: 10.1016/j.bioactmat.2020.09.006.

Panseri S, Cunha C, D'Alessandro T, Sandri M, Giavaresi G, Marcacci M, Hung CT, Tampieri A (2012) Intrinsically superparamagnetic Fe-hydroxyapatite nanoparticles positively influence osteoblast-like cell behaviour. *Journal of Nanobiotechnology* 10: 32. DOI: 10.1186/1477-3155-10-32.

Pant A, Singh J, Barnwal RP, Singh G, Singh B (2023) Theranostic Approach for the Management of Osteoporosis. *Critical Reviews in Therapeutic Drug Carrier Systems* 40: 95-121. DOI: 10.1615/CritRevTherDrugCarrierSyst.2022043413.

Papadimitriou N, Thorfve A, Brantsing C, Junevik K, Baranto A, Barreto Henriksson H (2014) Cell viability and chondrogenic differentiation capability of human mesenchymal stem cells after iron labeling with iron su-



crose. *Stem Cells and Development* 23: 2568-2580. DOI: 10.1089/scd.2014.0153.

Park J, An K, Hwang Y, Park JG, Noh HJ, Kim JY, Park JH, Hwang NM, Hyeon T (2004) Ultra-large-scale syntheses of monodisperse nanocrystals. *Nature Materials* 3: 891-895. DOI: 10.1038/nmat1251.

Park JH, von Maltzahn G, Zhang L, Schwartz MP, Ruoslahti E, Bhatia SN, Sailor MJ (2008) Magnetic Iron Oxide Nanoworms for Tumor Targeting and Imaging. *Advanced Materials* (Deerfield Beach, Fla.) 20: 1630-1635. DOI: 10.1002/adma.200800004.

Partain BD, Unni M, Rinaldi C, Allen KD (2020) The clearance and biodistribution of magnetic composite nanoparticles in healthy and osteoarthritic rat knees. *Journal of Controlled Release: Official Journal of the Controlled Release Society* 321: 259-271. DOI: 10.1016/j.jconrel.2020.01.052.

Patil US, Adireddy S, Jaiswal A, Mandava S, Lee BR, Chrisey DB (2015) In Vitro/In Vivo Toxicity Evaluation and Quantification of Iron Oxide Nanoparticles. *International Journal of Molecular Sciences* 16: 24417-24450. DOI: 10.3390/ijms161024417.

Paun IA, Popescu RC, Calin BS, Mustaciosu CC, Diniescu M, Luculescu CR (2018) 3D Biomimetic Magnetic Structures for Static Magnetic Field Stimulation of Osteogenesis. *International Journal of Molecular Sciences* 19: 495. DOI: 10.3390/ijms19020495.

Pei W, Yusufu Y, Zhan Y, Wang X, Gan J, Zheng L, Wang P, Zhang K, Huang C (2023) Biosynthesizing lignin dehydrogenation polymer to fabricate hybrid hydrogel composite with hyaluronic acid for cartilage repair. *Advanced Composites and Hybrid Materials* 6: 180. DOI: 10.1007/s42114-023-00758-6.

Pereira C, Pereira AM, Fernandes C, Rocha M, Mendes R, Fernández-García MP, Guedes A, Tavares PB, Grenèche JM, Araújo JP, Freire C (2012) Superparamagnetic MFe<sub>2</sub>O<sub>4</sub> (M = Fe, Co, Mn) nanoparticles: Tuning the particle size and magnetic properties through a novel one-step coprecipitation route. *Chemistry of Materials* 24: 1496-1504. DOI: 10.1021/cm300301c.

Petcharoen K, Sirivat A (2012) Synthesis and characterization of magnetite nanoparticles via the chemical coprecipitation method. *Materials Science and Engineering: B* 177: 421-427. DOI: 10.1016/j.mseb.2012.01.003.

Prieto-Alhambra D, Judge A, Javaid MK, Cooper C, Diez-Perez A, Arden NK (2014) Incidence and risk factors for clinically diagnosed knee, hip and hand osteoarthritis: influences of age, gender and osteoarthritis affecting other joints. *Annals of the Rheumatic Diseases* 73: 1659-1664. DOI: 10.1136/annrheumdis-2013-203355.

Puscasu E, Sacarescu L, Lupu N, Grigoras M, Oanca G, Balasoiu M, Creanga D (2016) Iron oxide-silica nanocomposites yielded by chemical route and sol-gel method. *Journal of Sol-Gel Science and Technology* 79: 457-465. DOI: 10.1007/s10971-016-3996-1.

Rahman MM, Nguyen C, Yan Z, Bolding M, Meford OT (2024) Synthesis of iron oxide nanocubes and their incorporation with luminescent lanthanide (Ln = Tb/ Eu)-Terephthalate complex in silica nanospheres using a reverse microemulsion method. *Journal of Solid State Chemistry* 329: 124406. DOI: 10.1016/j.jssc.2023.124406.

Ramaswamy S, Greco JB, Uluer MC, Zhang Z, Zhang Z, Fishbein KW, Spencer RG (2009) Magnetic resonance imaging of chondrocytes labeled with superparamagnetic iron oxide nanoparticles in tissue-engineered cartilage. *Tissue Engineering. Part a* 15: 3899-3910. DOI: 10.1089/ten.tea.2008.0677.

Ran Q, Xiang Y, Liu Y, Xiang L, Li F, Deng X, Xiao Y, Chen L, Chen L, Li Z (2015) Eryptosis Indices as a Novel Predictive Parameter for Biocompatibility of Fe<sub>3</sub>O<sub>4</sub> Magnetic Nanoparticles on Erythrocytes. *Scientific Reports* 5: 16209. DOI: 10.1038/srep16209.

Rana S, Chawla R, Kumar R, Singh S, Zheleva A, Dimitrova Y, Gadjeva V, Arora R, Sultana S, Sharma RK (2010) Electron paramagnetic resonance spectroscopy in radiation research: Current status and perspectives. *Journal of Pharmacy & Bioallied Sciences* 2: 80-87. DOI: 10.4103/0975-7406.67006.

Remya NS, Syama S, Sabareeswaran A, Mohanan PV (2016) Toxicity, toxicokinetics and biodistribution of dextran stabilized Iron oxide Nanoparticles for biomedical applications. *International Journal of Pharmaceutics* 511: 586-598. DOI: 10.1016/j.ijpharm.2016.06.119.

Revathy R, Sajini T, Augustine C, Joseph N (2023) Iron-based magnetic nanomaterials: Sustainable approaches of synthesis and applications. *Results in Engineering* 18: 101114. DOI: 10.1016/j.rineng.2023.101114.

Riegler J, Liew A, Hynes SO, Ortega D, O'Brien T, Day RM, Richards T, Sharif F, Pankhurst QA, Lythgoe MF (2013) Superparamagnetic iron oxide nanoparticle targeting of MSCs in vascular injury. *Biomaterials* 34: 1987-1994. DOI: 10.1016/j.biomaterials.2012.11.040.

Roy E, Patra S, Madhuri R, Sharma PK (2016) Stimuli-responsive poly(N-isopropyl acrylamide)-co-tyrosine@gadolinium: Iron oxide nanoparticle-based nanotheranostic for cancer diagnosis and treatment. *Colloids and Surfaces. B, Biointerfaces* 142: 248-258. DOI: 10.1016/j.colsurfb.2016.02.053.

Roy SD, Das KC, Dhar SS (2021) Conventional to green synthesis of magnetic iron oxide nanoparticles; its application as catalyst, photocatalyst and toxicity: A short review. *Inorganic Chemistry Communications* 134: 109050. DOI: 10.1016/j.inoche.2021.109050.

Sadeghzadeh H, Dianat-Moghadam H, Del Bakhshayesh AR, Mohammadnejad D, Mehdipour A (2023) A review on the effect of nanocomposite scaffolds reinforced with magnetic nanoparticles in osteogenesis and healing of bone injuries. *Stem Cell Research & Therapy* 14: 194. DOI: 10.1186/s13287-023-03426-0.

Saha S, Yang XB, Tanner S, Curran S, Wood D,

- Kirkham J (2013) The effects of iron oxide incorporation on the chondrogenic potential of three human cell types. *Journal of Tissue Engineering and Regenerative Medicine* 7: 461-469. DOI: 10.1002/term.544.
- Saldanha KJ, Piper SL, Ainslie KM, Kim HT, Majumdar S (2008) Magnetic resonance imaging of iron oxide labelled stem cells: applications to tissue engineering based regeneration of the intervertebral disc. *European Cells & Materials* 16: 17-25. DOI: 10.22203/ecm.v016a03.
- Saleh A, Hegde VV, Potty AG, Lane JM (2013) Bisphosphonate therapy and atypical fractures. *The Orthopedic Clinics of North America* 44: 137-151. DOI: 10.1016/j.ocl.2013.01.001.
- Samrot A V., Sahithya CS, Selvarani A J, Purayil SK, Ponnaiah P (2021) A review on synthesis, characterization and potential biological applications of superparamagnetic iron oxide nanoparticles. *Current Research in Green and Sustainable Chemistry* 4: 100042. DOI: 10.1016/j.crgsc.2020.100042.
- Saritas EU, Goodwill PW, Croft LR, Konkle JJ, Lu K, Zheng B, Conolly SM (2013) Magnetic particle imaging (MPI) for NMR and MRI researchers. *Journal of Magnetic Resonance (San Diego, Calif.: 1997)* 229: 116-126. DOI: 10.1016/j.jmr.2012.11.029.
- Schilcher J, Michaëlsson K, Aspenberg P (2011) Bisphosphonate use and atypical fractures of the femoral shaft. *The New England Journal of Medicine* 364: 1728-1737. DOI: 10.1056/NEJMoa1010650.
- Shah YY, Maldonado-Camargo L, Patel NS, Biedrzycki AH, Yarmola EG, Dobson J, Rinaldi C, Allen KD (2017) Magnetic particle translation as a surrogate measure for synovial fluid mechanics. *Journal of Biomechanics* 60: 9-14. DOI: 10.1016/j.jbiomech.2017.05.015.
- Sharifi I, Shokrollahi H, Amiri S (2012) Ferrite-based magnetic nanofluids used in hyperthermia applications. *Journal of Magnetism and Magnetic Materials* 324: 903-915. DOI: 10.1016/j.jmmm.2011.10.017.
- Sharouf H, Saffour Z (2024) Synthesizing and Using Iron Oxide Nanoparticles as Nanocomposite in Cotton Fabrics Nanofinishing. *Baghdad Science Journal* 21: 0072. DOI: 10.21123/bsj.2023.7743.
- Shavlovskaya OA, Gromova OA, Kochish AY, Yukhnovskaya YD, Romanov ID, Bokova IA (2023) Disease-modifying osteoarthritis drugs (DMOADs): new trends in osteoarthritis therapy. *FARMAKOEKONOMIKA. Modern Pharmacoeconomics and Pharmacoepidemiology* 16: 482-499. DOI: 10.17749/2070-4909/farmakoeconomika.2023.207.
- Shen J, Lan Y, Ji Z, Liu H (2024) Sirtuins in intervertebral disc degeneration: current understanding. *Molecular Medicine (Cambridge, Mass.)* 30: 44. DOI: 10.1186/s10020-024-00811-0.
- Shi C, Li Y, Gu N (2020) Iron-Based Nanozymes in Disease Diagnosis and Treatment. *Chembiochem: a European Journal of Chemical Biology* 21: 2722-2732. DOI: 10.1002/cbic.202000094.
- Shi SF, Jia JF, Guo XK, Zhao YP, Chen DS, Guo YY, Cheng T, Zhang XL (2012) Biocompatibility of chitosan-coated iron oxide nanoparticles with osteoblast cells. *International Journal of Nanomedicine* 7: 5593-5602. DOI: 10.2147/IJN.S34348.
- Son B, Kim HD, Kim M, Kim JA, Lee J, Shin H, Hwang NS, Park TH (2015) Physical Stimuli-Induced Chondrogenic Differentiation of Mesenchymal Stem Cells Using Magnetic Nanoparticles. *Advanced Healthcare Materials* 4: 1339-1347. DOI: 10.1002/adhm.201400835.
- Suh SK, Yuet K, Hwang DK, Bong KW, Doyle PS, Hatton TA (2012) Synthesis of nonspherical superparamagnetic particles: in situ coprecipitation of magnetic nanoparticles in microgels prepared by stop-flow lithography. *Journal of the American Chemical Society* 134: 7337-7343. DOI: 10.1021/ja209245v.
- Sun DY, Wu WB, Wu JJ, Shi Y, Xu JJ, Ouyang SX, Chi C, Shi Y, Ji QX, Miao JH, Fu JT, Tong J, Zhang PP, Zhang JB, Li ZY, Qu LF, Shen FM, Li DJ, Wang P (2024) Pro-ferroptotic signaling promotes arterial aging via vascular smooth muscle cell senescence. *Nature Communications* 15: 1429. DOI: 10.1038/s41467-024-45823-w.
- Suryadevara V, Hajipour MJ, Adams LC, Aissaoui NM, Rashidi A, Kiru L, Theruvath AJ, Huang CH, Maruyama M, Tsubosaka M, Lyons JK, Wu WE, Roudi R, Goodman SB, Daldrup-Link HE (2023) MegaPro, a clinically translatable nanoparticle for in vivo tracking of stem cell implants in pig cartilage defects. *Theranostics* 13: 2710-2720. DOI: 10.7150/thno.82620.
- Ta K, Chen S, Du M, Li J, Xu H, Liu S, Chen W, Wu Z, Peng X (2024) Iron oxides (oxyhydroxides) associated with biogenic iron-organic framework structures in deep-sea hydrothermal vents of the Indian Ocean. *Chemical Geology* 650: 121980. DOI: 10.1016/j.chemgeo.2024.121980.
- Talebloo N, Gudi M, Robertson N, Wang P (2020) Magnetic Particle Imaging: Current Applications in Biomedical Research. *Journal of Magnetic Resonance Imaging: JMRI* 51: 1659-1668. DOI: 10.1002/jmri.26875.
- Teschke R (2024) Hemochromatosis: Ferroptosis, ROS, Gut Microbiome, and Clinical Challenges with Alcohol as Confounding Variable. *International Journal of Molecular Sciences* 25: 2668. DOI: 10.3390/ijms25052668.
- Tran HV, Ngo NM, Medhi R, Srinoi P, Liu T, Ritikulsittichai S, Lee TR (2022) Multifunctional Iron Oxide Magnetic Nanoparticles for Biomedical Applications: A Review. *Materials (Basel, Switzerland)* 15: 503. DOI: 10.3390/ma15020503.
- Tran N, Hall D, Webster TJ (2012) Mechanisms of enhanced osteoblast gene expression in the presence of hydroxyapatite coated iron oxide magnetic nanoparticles. *Nanotechnology* 23: 455104. DOI: 10.1088/0957-4484/23/45/455104.
- Tran N, Webster TJ (2011) Increased osteoblast func-

tions in the presence of hydroxyapatite-coated iron oxide nanoparticles. *Acta Biomaterialia* 7: 1298-1306. DOI: 10.1016/j.actbio.2010.10.004.

Tran N, Webster TJ (2013) Understanding magnetic nanoparticle osteoblast receptor-mediated endocytosis using experiments and modeling. *Nanotechnology* 24: 185102. DOI: 10.1088/0957-4484/24/18/185102.

Vallabani NVS, Singh S, Karakoti AS (2019) Magnetic Nanoparticles: Current Trends and Future Aspects in Diagnostics and Nanomedicine. *Current Drug Metabolism* 20: 457-472. DOI: 10.2174/1389200220666181122124458.

Vergnaud F, Kesse X, Jacobs A, Pertion F, Begin-Colin S, Mertz D, Descamps S, Vichery C, Nedelec JM (2022) Magnetic bioactive glass nano-heterostructures: a deeper insight into magnetic hyperthermia properties in the scope of bone cancer treatment. *Biomaterials Science* 10: 3993-4007. DOI: 10.1039/d2bm00319h.

Vidya Balakrishnan PV, Gajski G, Chitra KC (2024) The effects of iron oxide nanoparticles on antioxidant capacity and response to oxidative stress in Mozambique tilapia (*Oreochromis mossambicus*, Peters 1852). *Arhiv Za Higijenu Rada i Toksikologiju* 75: 125-136. DOI: 10.2478/aiht-2024-75-3826.

Vinod E, James JV, Kachroo U, Sathishkumar S, Livingston A, Ramasamy B (2019) Comparison of incremental concentrations of micron-sized superparamagnetic iron oxide for labelling articular cartilage derived chondroprogenitors. *Acta Histochemica* 121: 791-797. DOI: 10.1016/j.acthis.2019.07.004.

Wahfiudin A, Pramata AD, Wicaksono ST, Ng QH, Hoo PY, Enche Ab Rahim SK, Jamalludin MR, Nasib AM (2024) Parameters adjustments for facile synthesis of high magnetization iron oxide nanoparticles from natural sand. *Nano-Structures and Nano-Objects* 37: 101114. DOI: 10.1016/j.nanoso.2024.101114.

Wang G, Xu W, Zhang J, Tang T, Chen J, Fan C (2021a) Induction of Bone Remodeling by Raloxifene-Doped Iron Oxide Functionalized with Hydroxyapatite to Accelerate Fracture Healing. *Journal of Biomedical Nanotechnology* 17: 932-941. DOI: 10.1166/jbn.2021.3068.

Wang H, Ge Y, Sun J, Wang H, Gu N (2020) Magnetic sensor based on image processing for dynamically tracking magnetic moment of single magnetic mesenchymal stem cell. *Biosensors & Bioelectronics* 169: 112593. DOI: 10.1016/j.bios.2020.112593.

Wang N, Xie Y, Xi Z, Mi Z, Deng R, Liu X, Kang R, Liu X (2022a) Hope for bone regeneration: The versatility of iron oxide nanoparticles. *Frontiers in Bioengineering and Biotechnology* 10: 937803. DOI: 10.3389/fbioe.2022.937803.

Wang S, He H, Mao Y, Zhang Y, Gu N (2024a) Advances in Atherosclerosis Theranostics Harnessing Iron Oxide-Based Nanoparticles. *Advanced Science (Weinheim, Baden-Wuerttemberg, Germany)* 11: e2308298. DOI:

10.1002/adv.202308298.

Wang T, Zhao H, Jing S, Fan Y, Sheng G, Ding Q, Liu C, Wu H, Liu Y (2023a) Magnetofection of miR-21 promoted by electromagnetic field and iron oxide nanoparticles via the p38 MAPK pathway contributes to osteogenesis and angiogenesis for intervertebral fusion. *Journal of Nanobiotechnology* 21: 27. DOI: 10.1186/s12951-023-01789-3.

Wang T, Zhao H, Zhang Y, Liu Y, Liu J, Chen G, Duan K, Li Z, Hui HPJ, Yan J (2024b) A novel extracellular vesicles production system harnessing matrix homeostasis and macrophage reprogramming mitigates osteoarthritis. *Journal of Nanobiotechnology* 22: 79. DOI: 10.1186/s12951-024-02324-8.

Wang X, Cao Q, Wu S, Bahrani Fard MR, Wang N, Cao J, Zhu W (2022b) Magnetic Nano-Platform Enhanced iPSC-Derived Trabecular Meshwork Delivery and Tracking Efficiency. *International Journal of Nanomedicine* 17: 1285-1307. DOI: 10.2147/IJN.S346141.

Wang X, Wang Q, Li G, Xu H, Liu B, Yuan B, Zhou Y, Li Y (2024c) Identifying the protective effects of miR-874-3p/ATF3 axis in intervertebral disc degeneration by single-cell RNA sequencing and validation. *Journal of Cellular and Molecular Medicine* 28: e18492. DOI: 10.1111/jcmm.18492.

Wang Y, Liu X, Ma S, He X, Guo C, Liang Z, Hu Y, Wei Y, Lian X, Huang D (2023b) Progress in cancer therapy with functionalized Fe<sub>3</sub>O<sub>4</sub> nanomaterials. *Frontiers of Materials Science* 17: 230658. DOI: 10.1007/s11706-023-0658-4.

Wang YJ, Lin PY, Hsieh SL, Kirankumar R, Lin HY, Li JH, Chen YT, Wu HM, Hsieh S (2021b) Utilizing Edible Agar as a Carrier for Dual Functional Doxorubicin-Fe<sub>3</sub>O<sub>4</sub> Nanotherapy Drugs. *Materials (Basel, Switzerland)* 14: 1824. DOI: 10.3390/ma14081824.

Waqas M, Niaz S, Batoo KM, Xu YB, Noor H, Ahmad N, Atiq S, Naseem S, Riaz S (2024) Exploring the microwave assisted sol-gel synthesized multivalent doped thin films of iron oxide for detailed impedance and magnetodielectric response. *Solid State Sciences* 149: 107441. DOI: 10.1016/j.solidstatesciences.2024.107441.

Wei W, Cai M, Yu S, Chen H, Luo Y, Zhang X (2022) Effect of Magnetic Nanoparticles on Hormone Level Changes During Perimenopausal Period and Regulation of Bone Metabolism. *Cellular and Molecular Biology (Noisy-le-Grand, France)* 68: 91-96. DOI: 10.14715/cmb/2022.68.12.17.

Wu J, Wu C, Cai Z, Gu H, Liu L, Xia C, Lui S, Gong Q, Song B, Ai H (2023) Ultra-small superparamagnetic iron oxide nanoparticles for intra-articular targeting of cartilage in early osteoarthritis. *Regenerative Biomaterials* 10: rbad052. DOI: 10.1093/rb/rbad052.

Wu S, Sun A, Zhai F, Wang J, Xu W, Zhang Q, Volinsky AA (2011) Fe<sub>3</sub>O<sub>4</sub> magnetic nanoparticles synthesis from tailings by ultrasonic chemical co-

precipitation. *Materials Letters* 65: 1882-1884. DOI: [10.1016/j.matlet.2011.03.065](https://doi.org/10.1016/j.matlet.2011.03.065).

Wu W, Wu Z, Yu T, Jiang C, Kim WS (2015) Recent progress on magnetic iron oxide nanoparticles: synthesis, surface functional strategies and biomedical applications. *Science and Technology of Advanced Materials* 16: 023501. DOI: [10.1088/1468-6996/16/2/023501](https://doi.org/10.1088/1468-6996/16/2/023501).

Xia Y, Guo Y, Yang Z, Chen H, Ren K, Weir MD, Chow LC, Reynolds MA, Zhang F, Gu N, Xu HHK (2019a) Iron oxide nanoparticle-calcium phosphate cement enhanced the osteogenic activities of stem cells through WNT/ $\beta$ -catenin signaling. *Materials Science & Engineering. C, Materials for Biological Applications* 104: 109955. DOI: [10.1016/j.msec.2019.109955](https://doi.org/10.1016/j.msec.2019.109955).

Xia Y, Zhao Y, Zhang F, Chen B, Hu X, Weir MD, Schneider A, Jia L, Gu N, Xu HHK (2019b) Iron oxide nanoparticles in liquid or powder form enhanced osteogenesis via stem cells on injectable calcium phosphate scaffold. *Nanomedicine: Nanotechnology, Biology, and Medicine* 21: 102069. DOI: [10.1016/j.nano.2019.102069](https://doi.org/10.1016/j.nano.2019.102069).

Xie M, Luo S, Li Y, Lu L, Deng C, Cheng Y, Yin F (2019) Intra-articular tracking of adipose-derived stem cells by chitosan-conjugated iron oxide nanoparticles in a rat osteoarthritis model. *RSC Advances* 9: 12010-12019. DOI: [10.1039/c8ra09570a](https://doi.org/10.1039/c8ra09570a).

Xin J, Wang Y, Zheng Z, Wang S, Na S, Zhang S (2022) Treatment of Intervertebral Disc Degeneration. *Orthopaedic Surgery* 14: 1271-1280. DOI: [10.1111/os.13254](https://doi.org/10.1111/os.13254).

Yang G, Ma W, Zhang B, Xie Q (2016) The labeling of stem cells by superparamagnetic iron oxide nanoparticles modified with PEG/PVP or PEG/PEI. *Materials Science & Engineering. C, Materials for Biological Applications* 62: 384-390. DOI: [10.1016/j.msec.2016.01.090](https://doi.org/10.1016/j.msec.2016.01.090).

Yang L, Tucker IG, Østergaard J (2011) Effects of bile salts on propranolol distribution into liposomes studied by capillary electrophoresis. *Journal of Pharmaceutical and Biomedical Analysis* 56: 553-559. DOI: [10.1016/j.jpba.2011.06.020](https://doi.org/10.1016/j.jpba.2011.06.020).

Yang W, Zheng Y, Chen J, Zhu Q, Feng L, Lan Y, Zhu P, Tang S, Guo R (2019a) Preparation and characterization of the collagen/cellulose nanocrystals/USPIO scaffolds loaded kartogenin for cartilage regeneration. *Materials Science & Engineering. C, Materials for Biological Applications* 99: 1362-1373. DOI: [10.1016/j.msec.2019.02.071](https://doi.org/10.1016/j.msec.2019.02.071).

Yang W, Zhu P, Huang H, Zheng Y, Liu J, Feng L, Guo H, Tang S, Guo R (2019b) Functionalization of Novel Theranostic Hydrogels with Kartogenin-Grafted USPIO Nanoparticles to Enhance Cartilage Regeneration. *ACS Applied Materials & Interfaces* 11: 34744-34754. DOI: [10.1021/acsami.9b12288](https://doi.org/10.1021/acsami.9b12288).

Yang Y, Liu Y, Song L, Cui X, Zhou J, Jin G, Boccaccini AR, Virtanen S (2023) Iron oxide nanoparticle-based nanocomposites in biomedical application. *Trends in Biotechnology* 41: 1471-1487. DOI: [10.1016/j.tibtech.2023.06.001](https://doi.org/10.1016/j.tibtech.2023.06.001).

Yang Z, Wu S, Gao Y, Kou D, Lu K, Chen C, Zhou Y, Zhou D, Chen L, Ge J, Li C, Zeng J, Gao M (2024) Unveiling the Biologically Dynamic Degradation of Iron Oxide Nanoparticles via a Continuous Flow System. *Small Methods* 8: e2301479. DOI: [10.1002/smt.202301479](https://doi.org/10.1002/smt.202301479).

Yao D, Liu NN, Mo BW (2020) Assessment of proliferation, migration and differentiation potentials of bone marrow mesenchymal stem cells labeling with silica-coated and amine-modified superparamagnetic iron oxide nanoparticles. *Cytotechnology* 72: 513-525. DOI: [10.1007/s10616-020-00397-5](https://doi.org/10.1007/s10616-020-00397-5).

Yarmola EG, Shah Y, Arnold DP, Dobson J, Allen KD (2016) Magnetic Capture of a Molecular Biomarker from Synovial Fluid in a Rat Model of Knee Osteoarthritis. *Annals of Biomedical Engineering* 44: 1159-1169. DOI: [10.1007/s10439-015-1371-y](https://doi.org/10.1007/s10439-015-1371-y).

Yu P, Zheng L, Wang P, Chai S, Zhang Y, Shi T, Zhang L, Peng R, Huang C, Guo B, Jiang Q (2020) Development of a novel polysaccharide-based iron oxide nanoparticle to prevent iron accumulation-related osteoporosis by scavenging reactive oxygen species. *International Journal of Biological Macromolecules* 165: 1634-1645. DOI: [10.1016/j.ijbiomac.2020.10.016](https://doi.org/10.1016/j.ijbiomac.2020.10.016).

Zhang G, Zhen C, Yang J, Zhang Z, Wu Y, Che J, Shang P (2022) 1-2 T static magnetic field combined with Ferumoxytol prevent unloading-induced bone loss by regulating iron metabolism in osteoclastogenesis. *Journal of Orthopaedic Translation* 38: 126-140. DOI: [10.1016/j.jot.2022.10.007](https://doi.org/10.1016/j.jot.2022.10.007).

Zhang X, Chen J, Jiang Q, Ding X, Li Y, Chen C, Yang W, Chen S (2020) Highly biosafe biomimetic stem cell membrane-disguised nanovehicles for cartilage regeneration. *Journal of Materials Chemistry. B* 8: 8884-8893. DOI: [10.1039/d0tb01686a](https://doi.org/10.1039/d0tb01686a).

Zhang Y, Wang Y, Zhu A, Yu N, Xia J, Li J (2024) Dual-Targeting Biomimetic Semiconducting Polymer Nanocomposites for Amplified Theranostics of Bone Metastasis. *Angewandte Chemie (International Ed. in English)* 63: e202310252. DOI: [10.1002/anie.202310252](https://doi.org/10.1002/anie.202310252).

Zheng B, von See MP, Yu E, Gunel B, Lu K, Vazin T, Schaffer DV, Goodwill PW, Conolly SM (2016) Quantitative Magnetic Particle Imaging Monitors the Transplantation, Biodistribution, and Clearance of Stem Cells In Vivo. *Theranostics* 6: 291-301. DOI: [10.7150/thno.13728](https://doi.org/10.7150/thno.13728).

Zheng L, Lu G, Pei W, Yan W, Li Y, Zhang L, Huang C, Jiang Q (2021a) Understanding the relationship between the structural properties of lignin and their biological activities. *International Journal of Biological Macromolecules* 190: 291-300. DOI: [10.1016/j.ijbiomac.2021.08.168](https://doi.org/10.1016/j.ijbiomac.2021.08.168).

Zheng L, Yu P, Zhang Y, Wang P, Yan W, Guo B, Huang C, Jiang Q (2021b) Evaluating the bio-application of biomacromolecule of lignin-carbohydrate complexes (LCC) from wheat straw in bone metabolism via ROS scavenging. *International Journal of Biological Macromolecules* 176: 13-25. DOI: [10.1016/j.ijbiomac.2021.08.168](https://doi.org/10.1016/j.ijbiomac.2021.08.168).

10.1016/j.ijbiomac.2021.01.103.

Zheng L, Zhao S, Li Y, Xu J, Yan W, Guo B, Xu J, Jiang L, Zhang Y, Wei H, Jiang Q (2024) Engineered MgO nanoparticles for cartilage-bone synergistic therapy. *Science Advances* 10: eadk6084. DOI: 10.1126/sciadv.adk6084.

Zheng L, Zhuang Z, Li Y, Shi T, Fu K, Yan W, Zhang L, Wang P, Li L, Jiang Q (2022) Bone targeting antioxidative nano-iron oxide for treating postmenopausal osteoporosis. *Bioactive Materials* 14: 250-261. DOI: 10.1016/j.bioactmat.2021.11.012.

Zhi D, Yang T, Yang J, Fu S, Zhang S (2020) Targeting strategies for superparamagnetic iron oxide nanoparticles in cancer therapy. *Acta Biomaterialia* 102: 13-34. DOI: 10.1016/j.actbio.2019.11.027.

Zhong D, Zhao J, Li Y, Qiao Y, Wei Q, He J, Xie T, Li W, Zhou M (2019) Laser-triggered aggre-

gated cubic  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>@Au nanocomposites for magnetic resonance imaging and photothermal/enhanced radiation synergistic therapy. *Biomaterials* 219: 119369. DOI: 10.1016/j.biomaterials.2019.119369.

Zhou H, Chen T, Wu A (2024) Effects of Oxidative Stress on Mitochondrial Functions and Intervertebral Disc Cells. *Sichuan Da Xue Xue Bao Yi Xue Ban* 55: 249-255. DOI: 10.12182/20240360201. (In Chinese)

Zhou W, Huang J, Xiao Q, Hu S, Li S, Zheng J, Du Z, Peng J, Chen H (2022) Glu-Urea-Lys Scaffold Functionalized Superparamagnetic Iron Oxide Nanoparticles Targeting PSMA for In Vivo Molecular MRI of Prostate Cancer. *Pharmaceutics* 14: 2051. DOI: 10.3390/pharmaceutics14102051.

**Editor's note:** The Scientific Editor responsible for this paper was Martin Stoddart.